



Bandgap-adjusted bismuth tungstate-titanium dioxide S-scheme heterojunctions: Optimizing interfacial electronic structure for rapid VOC mineralization

Qian Yin¹ · Hubdar Ali Maitlo¹ · Ki-Hyun Kim¹

Received: 31 March 2026 / Revised: 6 June 2026 / Accepted: 9 June 2026
© The Author(s) 2026

Abstract

To strategically overcome the shortcomings of conventional photocatalysts, particularly inadequate redox potentials, a series of precisely engineered $\text{TiO}_2\text{-Bi}_2\text{WO}_6$ heterojunction photocatalysts, coded as TB-x (x represents the molar ratio% of Bi: Ti), has been designed and synthesized through deliberate bandgap adjustment. An optimal interfacial electronic structure, formed by coupling wide-bandgap TiO_2 (3.0–3.2 eV) with narrower-bandgap Bi_2WO_6 (2.6–2.9 eV), enables efficient charge dynamics under low-intensity UV irradiation (~ 1 W). The optimized TB-5 demonstrates complete removal of 5 ppm formaldehyde (FA: 100% X_{FA}) within 600 s, achieving a clean air delivery rate of 10.37 L min^{-1} and apparent quantum yield of 2.68E-01%. The exceptional activity is supported by the formation of a robust S-scheme heterojunction, as confirmed both experimentally and theoretically via density functional theory calculations. This charge preservation mechanism is remarkably robust, converting 81.6% of FA (initial concentration: 100 ppm) into CO_2 within 2 h. In-situ DRIFTS analysis further suggests that FA oxidation proceeds sequentially through dioxymethylene and formate intermediates. This work thus establishes a foundational strategy for practical indoor air purification by integrating advanced S-scheme design with atomic-level mechanistic insight, charting a clear path from lab-scale discovery to real-world application.

Keywords Formaldehyde · Photocatalytic air purification · $\text{TiO}_2\text{-Bi}_2\text{WO}_6$ S-scheme · Charge transfer and reaction mechanism

1 Introduction

Formaldehyde (FA), a colorless gas at room temperature, is one of the most persistent indoor air pollutants [1, 2]. The high level of indoor FA concentration is typically associated with diverse sources such as cooking, smoking, building materials, and furniture [3–5]. Due to the widespread presence and significant adverse effects on human health, FA has often been taken as a priority target for indoor air pollution control. Given its harmful health impacts, the World Health Organization (WHO) has set a short-term (30-minute)

exposure limit of 0.1 mg m^{-3} (0.08 ppm) for indoor FA in 2010 [6]. Therefore, controlling FA levels in indoor air is essential for maintaining good air quality and safeguarding human health.

In recent years, photocatalytic degradation (PCD) technology has been widely applied for the treatment of gaseous pollutants due to its high efficiency, safety, stability, and low energy consumption. Photocatalysts can utilize light energy to decompose gaseous FA into harmless products such as water (H_2O) and carbon dioxide (CO_2) under ambient conditions [7]. TiO_2 is widely regarded as a benchmark photocatalytic semiconductor owing to its non-toxicity, low cost, and robust chemical stability [8]. However, its practical efficacy remains severely constrained by rapid photogenerated charge-carrier recombination and a restricted optical response limited to the ultraviolet region of the solar spectrum [9]. To mitigate these deficiencies, strategic modifications such as elemental doping and heterojunction

✉ Ki-Hyun Kim
kkim61@hanyang.ac.kr

¹ Department of Civil and Environmental Engineering,
Hanyang University, 222 Wangsimni-Ro, Seoul
04763, Republic of Korea

engineering have been extensively deployed to boost catalytic activity to mitigate these deficiencies, strategic modifications such as elemental doping and heterojunction engineering have been extensively deployed to enhance catalytic activity [10, 11]. Among these strategies, the emerging S-scheme heterojunction framework offers an elegant solution to the conventional trade-off between charge separation and redox capacity. Driven by an interface-induced internal electric field (IEF), the S-scheme configuration selectively guides the recombination of lower-energy conduction-band electrons from the oxidation photocatalyst with lower-energy valence-band holes from the reduction photocatalyst. This precise spatial charge separation successfully preserves both the powerful reduction potential of the remaining conduction-band electrons and the strong oxidation potential of the corresponding valence-band holes, maximizing overall photocatalytic performance [12].

In the context of FA PCD, maintaining this elevated oxidation potential is critical. By precisely aligning the band structures and expanding light-harvesting capacity, S-scheme heterojunction materials retains great potential to mitigate the intrinsic carrier recombination and optical absorption limitations (e.g., pristine TiO_2) [13]. These engineered S-scheme architectures exhibit clear superiority in FA degradation, offering accelerated reaction kinetics, high operational stability, and robust efficiency across diverse environmental matrices. Consequently, they establish a highly viable platform for advanced indoor air purification [14].

The utility of bismuth-based compounds, in a range of photocatalytic applications, from the oxidation of indoor organic air pollutants to CO_2 conversion and H_2 production, is well known and stems from their unique layered structure, high chemical stability, and strong optical properties [15, 16]. Bi_2WO_6 , a typical and simple Aurivillius oxide, possesses an orthorhombic structure composed of $[\text{Bi}_2\text{O}_2]^{2+}$ layers interconnected by $[\text{WO}_4]^{2-}$ layers [17]. This structure arrangement is an advantageous feature for the separation of photogenerated electron-hole pairs at coordinatively unsaturated surface sites. In addition, Bi_2WO_6 has a lower band-gap (i.e., 2.6–2.9 eV) because of a higher valence band (VB) and lower conduction band (CB) made of Bi 6s/O 2p orbitals and W 5d orbitals, respectively [18]. It enables visible-light response while retaining sufficient oxidation ability for reactive oxygen species (ROS) generation. These physico-chemical features render Bi_2WO_6 particularly suitable for gas-phase FA oxidation, enabling rapid oxygen activation, efficient use of surface hydroxyl species, and sustained oxidation of oxygenated intermediates. Therefore, forming an S-scheme heterojunction by coupling visible light-responsive Bi_2WO_6 with wide-bandgap TiO_2 (3.0–3.2 eV) is a proven strategy for enhancing photocatalytic performance.

Over the past few decades, TiO_2 - Bi_2WO_6 (TB) systems have been deployed for diverse applications, including wastewater remediation [19–21], photoelectric chemical conversion [22, 23], CO_2 methanation reaction [16, 24], and antibacterial application [25, 26]. Despite this diverse utility, its performance in simulated indoor environments has scarcely been explored.

To fill this research gap, this study systematically uncovers the fundamental mechanisms of gas-phase FA oxidation over TB-x composites. Although the feasibility of TB-x heterojunctions has been well established for aqueous applications, their operation in gas-phase environments has been poorly understood. Unlike aqueous systems, gas-phase photocatalysis faces major limitations: weaker reactant adsorption, shorter surface residence times, and the lack of a bulk solvent for continuous supply of hydroxyl precursor. Furthermore, these systems exhibit high sensitivity to relative humidity and the inhibitory accumulation of intermediates. Consequently, maximizing interfacial charge separation while preserving high redox potentials is more critical in gas-phase operations than in their liquid-phase counterparts [27, 28]. In this regard, this study presents two key advances: first, definitive proof of a high-performance S-scheme charge transfer mechanism is established, distinguishing it from conventional Type-II pathways. Second, the surface reaction pathway and key intermediates are elucidated in real-time. By integrating practical performance evaluation with advanced characterization tools, including UPS, in-situ XPS, EIS, and in-situ diffuse reflectance infrared Fourier transform spectroscopy (DRIFTS), coupled with theoretical density functional theory (DFT) simulations, we provide unequivocal evidence for the S-scheme pathway and track the mineralization process of FA.

To address these issues, this study carefully designs a series of TB-x heterojunctions by adjusting their band-gap alignment to create a robust S-scheme charge transfer structure. The novelty of this work lies in two key aspects. First, instead of relying solely on observations, we provide clear experimental and theoretical (DFT) evidence for the S-scheme pathway. We demonstrate how it preserves strong redox potential that enables rapid oxygen activation even under low-intensity light. Second, we use in-situ DRIFTS to create a real-time, molecular-level map of the formaldehyde breakdown process, identifying the key step where dioxymethylene transforms into formate intermediates. By connecting atomic-scale electronic tuning to practical performance metrics such as Clean Air Delivery Rate (CADR), this study establishes a foundational framework for designing high-performance, scalable S-scheme catalysts for sustainable indoor air purification.

2 Experiment

2.1 Materials and chemicals

AEROXIDE® TiO₂ P25 was procured from Evonik Industries AG (Essen, Germany). Bi(NO₃)₃·5H₂O (98%), Na₂WO₄·2H₂O (≥99%), and paraformaldehyde (pFA (95%)) were purchased from Sigma-Aldrich (St. Louis, Missouri, United States of America (USA)). Ethylene glycol (EG) was purchased from Daejung chemicals & metals Co., Ltd (Siheung, South Korea). Nitrogen (N₂ (99.999%)) and air (99.999%) cylinders were purchased from Union Gas Co., Ltd. (Yongin, South Korea). The FA gaseous primary standard (G-PS) was prepared by thermally decomposing pFA at 110 °C under an N₂ flow. The FA G-PS was stored in a polyester aluminum (PEA) bag. Honeycomb ceramic (HC) filters (55×55×10 cm (2 mm hole size)) were supplied by Pingxiang Zhongci Environmental Ceramics Material Co., Ltd. (Pingxiang, China).

2.2 Photocatalyst synthesis

The preparation of TiO₂-Bi₂WO₆ (TB-x) samples has been done by modifying the procedures reported previously [19]. Different quantities of Bi(NO₃)₃·5H₂O and Na₂WO₄·2H₂O were added to a 50 mL glass beaker containing 40 mL EG, to ensure the molar ratio of Bi(NO₃)₃·5H₂O and Na₂WO₄·2H₂O in a 2:1 ratio (Table S1). The solution was stirred for 5 min under ambient conditions. After that, 1 g TiO₂ was added to the above mixture solution and stirred continuously under ambient conditions for 180 min. The resultant suspension was then transferred to a stainless-steel autoclave and hydrothermally treated at 160 °C for 15 h. After cooling down to room temperature, the sample was centrifuged to collect the light-yellow slurry. This light-yellow slurry was washed with deionized (DI) water 3 times and then placed in a convection oven operated at 85 °C for 12 h to obtain the dry solid powder. The obtained dry powder was labeled x% TiO₂-Bi₂WO₆ (TB-x; where x denotes the molar ratio of Bi to Ti). The preparation of the Bi₂WO₆ follows a procedure analogous to that used for TB-x, with the distinction that TiO₂ is not introduced during the process. The final product is identified as Bi₂WO₆. The 20–100 mg of the TB-x photocatalyst was then added to a 500 mL glass beaker containing 100 mL DI water and the HC filter. The suspension was ultrasonicated for 120 min, and the glass beaker was then placed in a convection oven operated at 85 °C for 120 min to obtain the TB-x photocatalyst-loaded HC filter. Ultrasonication improved particle dispersion and promoted catalyst deposition within the porous HC channels, which enhanced contact between the catalyst and substrate. No binder was used to avoid pore blockage and active-site coverage. The

coating stability was evaluated by repeated photocatalytic runs and post-reaction inspection, during which there was no apparent catalyst detachment or powder shedding.

2.3 Photocatalyst characterization

A suite of analytical techniques was employed to characterize the TB-x composites and reference materials (TiO₂ and Bi₂WO₆), probing their crystal structure, elemental composition, surface properties, morphologies, and optoelectronic properties. Fourier transform infrared spectroscopy (FTIR (Nicolet™ iS50 FTIR spectrometer, Thermo Fisher Scientific, Waltham, Massachusetts, USA)) was utilized to identify the functional groups on the photocatalyst surfaces. The surface morphologies and the elemental distribution were analyzed using field emission scanning electron microscopy (SEM) fitted with an energy-dispersive X-ray spectroscopy (EDS) probe (Verios™ 5 XHR, Thermo Fisher Scientific, Waltham, Massachusetts, USA). The high-resolution transmission electron microscope (HR-TEM) images were obtained using a JEM-2100 F (JEOL Ltd., Tokyo, Japan). The surface properties (Brunauer-Emmett-Teller (BET) surface area and pore size distribution) of the tested photocatalysts were quantified using N₂ adsorption-desorption isotherms acquired at 77 K (3Flex, Micromeritics Instrument Corp., Norcross, Georgia, USA). The powder X-ray diffraction (PXRD) patterns (D8 ADVANCE, Bruker Corp., Billerica, Massachusetts, USA) were used to determine the crystal structures of the tested photocatalysts. The PXRD data were obtained in the 5–80° range using a scan speed and step size of 5° min⁻¹ and 0.2°, respectively.

UV-Visible diffuse reflectance (UV-Vis-DRS) measurements performed over a range of 200–800 nm with a Cary 5000 UV-Vis-near-infrared (NIR) spectrophotometer (Agilent Technologies, Inc., Santa Clara, California, USA) to characterize light absorption properties and photoluminescence (PL (FP-8200, Jasco International Co., Ltd., Tokyo, Japan)) spectroscopy were employed to determine the charge carrier recombination of the tested photocatalysts. X-ray photoelectron spectroscopy (XPS (K-alpha™ system, Thermo Fisher Scientific, Waltham, Massachusetts, USA)) was used to analyze the surface chemistry of the catalysts. The acquired XPS data were charge-corrected to 284.8 eV. An electrochemical workstation (VersaSTAT4, AMETEK Inc., Berwyn, Pennsylvania, USA) was employed to determine the transient photocurrent (PC) and electrochemical impedance spectra (EIS) of the tested photocatalysts. The electrochemical analysis was conducted in a three-electrode electrolytic cell with a quartz window. The working electrode consisted of TB-x coated fluorine-doped tin dioxide (FTO) conductive glass, the reference electrode was silver (Ag)/silver chloride (AgCl) (stored in 3.0 M KCl solution),

and the counter electrode was a platinum (Pt) wire. The electrolyte was a 0.5 mol L⁻¹ sodium sulfate (Na₂SO₄) solution. The external light source was a 10 W UV light-emitting diode (LED). The effective area of the working electrode was 2 cm × 2 cm area. The EIS was analyzed at an open circuit potential (1 V versus Ag/AgCl) with a frequency range of 0.01 Hz to 100 kHz. Likewise, the transient PC responses for photocatalysts were recorded at the potential of 1 V versus Ag/AgCl.

Electron paramagnetic resonance (EPR) spectrometry (EMXplus; Bruker Corp., Billerica, MA, USA) was used to evaluate the generated reactive oxygen species (ROS) (e.g., superoxide [$\cdot\text{O}_2^-$] and hydroxide [$\cdot\text{OH}$] radicals) during PCO using 5,5-dimethyl-1-pyrroline N-oxide (DMPO) as the spin-trapping agent. The adsorption and photocatalytic oxidation mechanisms of FA on the best-performing photocatalyst were investigated using in-situ DRIFTS (Nicolet™ iS50, Thermo Scientific, USA) by tracking the evolution of surface UV light irradiation. This experimental sequence clarifies how the technique captures the dynamic transition from purely adsorbed intermediates to photoinduced reaction species and products.

2.4 Photocatalytic FA removal experiments

2.4.1 Setup and method

The experimental setup involved connecting the cord of the AP unit to a mobile power supply. A commercial FA sensor (TM-802, TENMARS Electronics Co., Ltd., Taipei, Taiwan (range: 0.01–5 ppm FA and 5–95% RH and accuracy: ± 5% of the reading (~ ± 0.03 ppm FA and ± 8% RH))) was placed near the AP unit for real-time monitoring of the varying FA concentration values within the chamber. The photocatalyst-loaded HC filter was installed in the AP unit. The chamber was flushed with air until the FA sensor registered at 0 ppm, after which a precise volume of DI H₂O and FA G-PS was introduced to maintain the selected RH levels inside the chamber. The photocatalytic oxidation of FA was conducted at room temperature (RT) and atmospheric pressure under UV irradiation (power = 0.98 W and $\lambda_{\text{max}} = 371$ nm). Subsequently, the FA removal performance of the best-performing TB-x photocatalyst was investigated as a function of various process variables such as m_{cat} (20–100 mg), AP flow rate (100–160 L min⁻¹), RH level (0–80%), FA concentration (1–5 ppm), O₂ content (0–21 vol%), and reuse cycles.

The produced CO₂ concentration (for calculating the CO₂ yield (Y_{CO_2})) was determined using a gas chromatograph (GC)-methanizer-flame ionization detector (FID) system (Nexis™ GC-2030, Shimadzu Corp., Kyoto, Japan). The Y_{CO_2} was quantified based on the CO_x signal in the chromatogram, as the photocatalytic FA oxidation experiments

were conducted with an excess O₂ concentration (21 vol%). The photocatalytic FA oxidation pathway was assessed using in-situ DRIFTS (Nicolet™ iS50 FTIR spectrometer (Thermo Fisher Scientific, Waltham, Massachusetts, USA) equipped with a diffuse reflectance cell (Praying Mantis™, Harrick Scientific Products Inc., Pleasantville, New York, USA). For in-situ DRIFTS analysis, a higher FA concentration (100 ppm, G-WS in air or N₂ at 0% RH) was employed to improve the detectability of adsorbed species and transient intermediates, which are often too weak to be resolved at trace-level concentrations. The photocatalyst (50 mg) was loaded into the cell and flushed with dry air at 100 mL min⁻¹ for 60 min prior to measurement. Spectra were collected sequentially: (1) background spectrum of the flushed catalyst; (2) spectra under dark conditions after exposure to the FA stream (100 mL min⁻¹) to monitor adsorption; and (3) spectra under UV irradiation at fixed time intervals to track the evolution of surface intermediates and products. All spectra were acquired at room temperature using identical acquisition parameters, and dark/UV datasets were referenced to the same background to enable direct comparison. Although the surface coverage of intermediates at 100 ppm is expected to be higher than under lower, more realistic concentrations, the DRIFTS experiment was designed to identify the dominant surface reaction pathway rather than to replicate the exact surface conditions during actual photocatalytic operation. Therefore, the intermediate evolution observed at 100 ppm is used here for mechanistic assignment, while the practical photocatalytic performance was evaluated separately under lower formaldehyde concentrations in the air purifier (AP) chamber tests.

2.4.2 Data analysis

FA removal efficiency (X_{FA} (%)) was calculated using Eq. 1. The kinetic reaction rate (r (mmol h⁻¹ g⁻¹)) was calculated using Eq. 3. The Eqs. 4 and 5 were used to calculate the apparent quantum yield (AQY (%)) and mass-normalized apparent quantum yield (MAQY (molecules photon⁻¹ g⁻¹)), respectively. The Eqs. 2, 6, and 7 were used to calculate the experimental decay constant (k_e), CADR (L min⁻¹), and specific CADR (SCADR, L min⁻¹ g⁻¹), respectively. The Eq. 8 was utilized to calculate the Y_{CO_2} . C_0 represents the initial FA concentration. C_t denotes the FA concentration at a specific time point. The k represents the decay constant (min⁻¹). The k_e denotes the experimental decay constant obtained by the generalized reduce-gradient non-linear regression fitting using Eq. 2. V represents the volume of the chamber (24 L). $\Delta C/\Delta t$ represents the FA decay rate. R and T denote the universal gas constant and temperature, respectively. k_n indicates the natural decay rate constant. F is the photon flux per second on the HC filter. C_d indicates the

CO₂ concentration at a specific time point. All experiments were conducted three times to ensure the reproducibility of the data. The error bars on the performance data indicate the standard deviation of triplicate runs.

$$X_{FA} = 100 * \frac{C_0 - C_t}{C_0} \quad (1)$$

$$C_t = C_0 e^{-kt} \quad (2)$$

$$r = 1000 * \frac{\Delta n}{m_{cat} * \Delta t} = 1000 * \frac{\Delta C * 10^{-6} * V}{m_{cat} * \Delta t * R * T} \quad (3)$$

$$AQY = \frac{Decay\ rate}{Photon\ flux} \times 100 \quad (4)$$

$$MAQY = \frac{AQY}{100 \times m_{cat}} \quad (5)$$

$$CADR = V * (k_e - k_n) \quad (6)$$

$$SCADR = \frac{CADR}{m_{cat}} \quad (7)$$

$$Y_{CO_2} = 100 * \frac{C_d}{C_0 - C_t} \quad (8)$$

2.5 DFT models and methods

All calculations were performed using density functional theory (DFT) as implemented in the Vienna Ab initio Simulation Package (VASP). The exchange-correlation functional was treated within the generalized gradient approximation using the Perdew-Burke-Ernzerhof parameterization (GGA-PBE). Interactions between ion cores and valence electrons were described by the projector augmented wave (PAW) method. A plane-wave cutoff energy of 450 eV was applied throughout. The Brillouin zone was sampled using Monkhorst-Pack k-point meshes of $2 \times 2 \times 1$ for structural relaxations and $2 \times 2 \times 1$ for electronic property calculations (along the non-periodic direction). These choices ensure total-energy changes < 5 meV atom⁻¹ upon further k-point refinement. Structural relaxations were conducted until the Hellmann-Feynman forces converged to below 0.02 eV/Å and the total energy change fell below 10^{-5} eV per step, with an electronic (SCF) convergence threshold of 10^{-6} eV.

To construct the heterojunction, Bi₂WO₆ (131) and TiO₂ (101) slabs were brought into registry to maximize interfacial contact while minimizing lattice strain. The smaller in-plane cell was isotropically stretched to achieve a lattice mismatch of $\leq 3\%$. Each slab contained a thickness equivalent to two stoichiometric formula-unit stacking blocks

and was separated by a 20 Å vacuum region to eliminate spurious interactions between periodic images. The bottom atomic layer of TiO₂ slab was fixed at bulk positions to mimic the support, while all other atoms in both slabs were fully relaxed. Because interfacial adhesion and adsorbate interactions involve dispersion forces, Grimme's DFT-D3 correction was applied to account for van der Waals interactions. GGA-PBE is known to underestimate band gaps. Therefore, single-point HSE06 hybrid-functional calculations were performed on the PBE-relaxed geometries to obtain more reliable band structures and projected densities of states (PDOS) for the analysis of optical/electronic properties. Band edges were referenced to vacuum using the planar-averaged electrostatic potential. From the optimized structures, we computed PDOS, work functions ($\Phi = V_{vac} - E_F$), and charge-density difference maps (CDD maps, $\Delta\rho = \rho(\text{TiO}_2\text{-Bi}_2\text{WO}_6) - \rho(\text{Bi}_2\text{WO}_6) - \rho(\text{TiO}_2)$). Electron localization functions (ELF) and all isosurface visualizations were visualized with the VESTA package.

3 Results and discussion


3.1 Physicochemical characteristics

The successful formation of the TB-x composite (e.g., TB-5) was confirmed through structural and chemical analysis. HRTEM (Fig. 1a-c) revealed the coexistence of hexagonal TiO₂ and nanosheet-like Bi₂WO₆, with lattice fringes of 0.314 nm (Bi₂WO₆ (131)) and 0.351 nm (TiO₂ (101)), confirming intimate contact. SAED and SEM-EDS (Fig. 1d, S1) further verified the polycrystalline nature and uniform distribution of Bi₂WO₆ on the TiO₂ surface.

BET analysis and corresponding pore-size distributions (Fig. 2a-b; Table 1) reveal distinct textural variations across the synthesized materials. Driven by its characteristic layered crystal structure, pristine Bi₂WO₆ exhibited the highest specific surface area (72.78 m² g⁻¹), pore volume (0.17 cm³ g⁻¹), and average pore size (5.22 nm). In comparison, pristine TiO₂ displayed lower textural parameters, specific surface area (49.3 m² g⁻¹), pore volume (0.07 cm³ g⁻¹), and average pore diameter (4.70 nm). Upon composite formation, the TB-x series followed a non-monotonic textural evolution dictated by the Bi₂WO₆ mass fraction.

At low loading thresholds (TB-2 and TB-5), specific surface areas marginally decreased to 46.03 m² g⁻¹ and 45.97 m² g⁻¹, respectively. This initial reduction suggests that localized Bi₂WO₆ nucleation partially masks the TiO₂ surface or shields its intrinsic micropore/small mesopore networks. Concurrently, however, pore volumes of TB-2 and TB-5 increased to 0.09 cm³ g⁻¹ and 0.08 cm³ g⁻¹, respectively, surpassing pristine TiO₂. This divergence confirms

Fig. 1 TEM micrographs of the tested photocatalysts: (a) Bi_2WO_6 , (b) TiO_2 , (c) TB-5, and (d) SAED pattern of TB-5

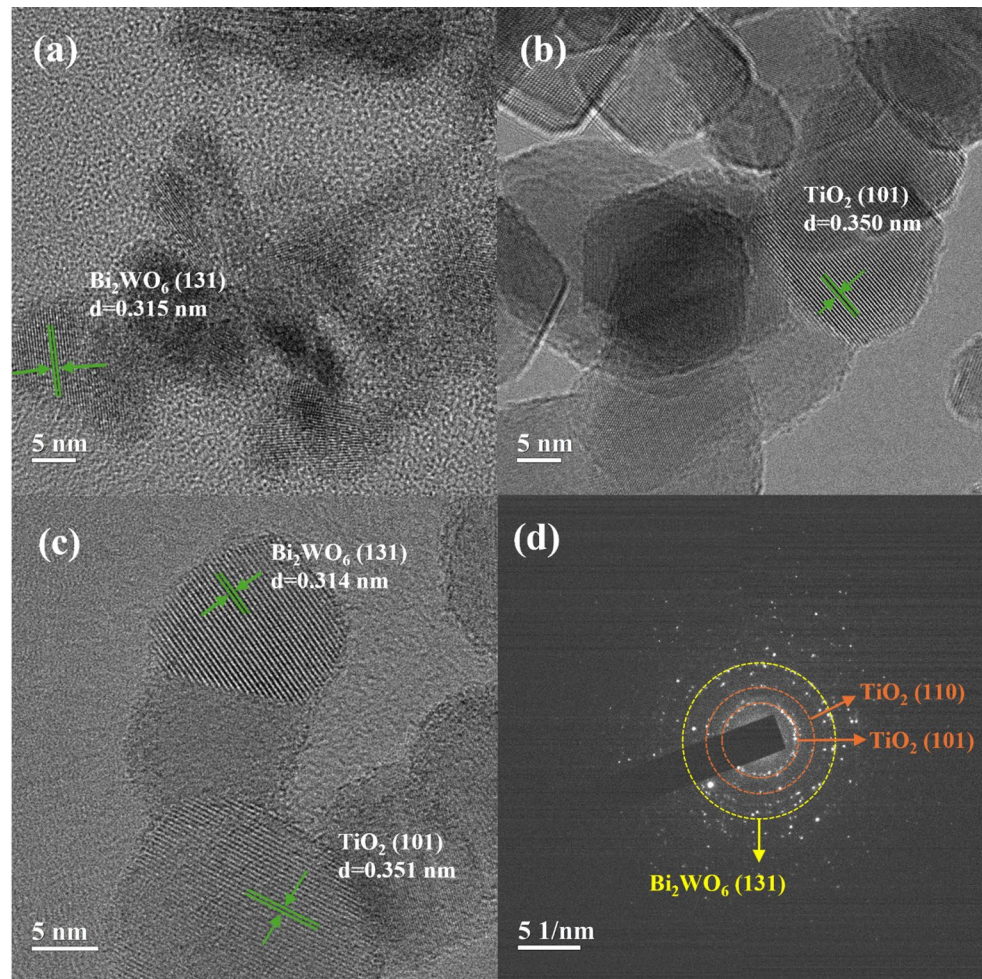

that the structural modification at low loadings involves a competitive interplay between localized pore blockage and the simultaneous creation of new interparticle voids or larger mesopores.

As the Bi_2WO_6 content increased further in TB-10, this trend shifted toward net structural optimization: specific surface area and pore volume rose to $52.55 \text{ m}^2 \text{ g}^{-1}$ and $0.11 \text{ cm}^3 \text{ g}^{-1}$, respectively, while pore diameter shifted to 5.19 nm , which lies between the values of pristine TiO_2 and pristine Bi_2WO_6 . This transition underscores a dominant structural contribution from the layered Bi_2WO_6 component at higher loadings, coupled with the proliferation of highly accessible interfacial mesopores at the TiO_2 - Bi_2WO_6 heterojunction. Collectively, the textural evolution progresses from a regime of balanced surface masking and interparticle void generation at low mass fractions (TB-2/TB-5) to a regime dominated by interfacial mesopore development and a shift toward Bi_2WO_6 -like porosity at elevated loadings (TB-10). The PXRD results for TB-x composite photocatalysts (e.g., TB-2, TB-5, TB-10) and their pristine counterparts (i.e., Bi_2WO_6 and TiO_2) are presented in Fig. 2c. The diffraction peaks of Bi_2WO_6 match well with its standard

pattern (JCPDS 39–0256). In the case of pristine Bi_2WO_6 , the main peaks appear at 28.3° , 32.8° , 47.0° , 55.9° , 58.5° , 68.8° , 76.0° , and 78.3° corresponding to the (131), (002), (202), (133), (262), (004), (391), and (204) crystal planes, respectively. These reflections are characteristic of orthorhombic Bi_2WO_6 , confirming that the synthesized Bi_2WO_6 retains its well-defined orthorhombic crystal structure [29]. Likewise, the diffraction peaks of TiO_2 align with its standard patterns (JCPDS 21–1272 and JCPDS 21–1276), indicating the presence of TiO_2 in the anatase and rutile phases [12]. The preservation of such crystalline phases of both materials indicates high structural stability, which is essential for maintaining lattice integrity and facilitating efficient interfacial contact in the subsequent formation of the TB-x S-scheme heterojunction. In the case of TB-x catalysts with higher Bi_2WO_6 content (i.e., TB-5 and TB-10), the characteristic Bi_2WO_6 diffraction peaks become more prominent in the XRD patterns (Fig. 2c).

Using the diffraction peak of TiO_2 (101) as a reference, the crystallinity index (CI) of pristine P25 was 99.4%. After heterojunction formation, the CI decreased to 98.5% for TB-2, 98.0% for TB-5, and 97.7% for TB-10. CI value was

Fig. 2 Surface properties of TB-x series catalysts, along with the reference materials (Bi_2WO_6 and TiO_2) tested as photocatalysts. (a) N_2 adsorption-desorption isotherms, (b) Pore size distribution curves, (c) PXRD patterns, and (d) FTIR patterns

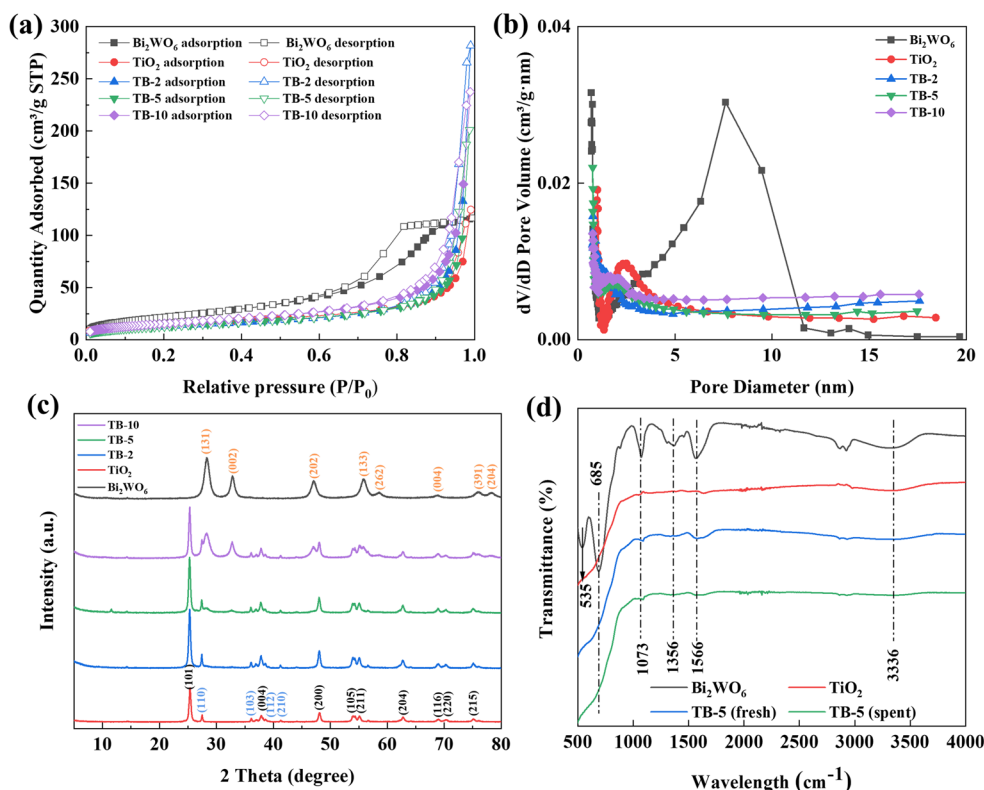


Table 1 Physical characteristics of TB-x series catalysts along with the reference materials (Bi_2WO_6 and TiO_2)

Order	Material	BET surface area $\text{m}^2 \text{g}^{-1}$	Total pore volume $\text{cm}^3 \text{g}^{-1}$	Average pore diameter nm
1	Bi_2WO_6	72.78	0.17	5.22
2	TiO_2	49.30	0.07	4.7
3	TB-2	46.03	0.09	4.68
4	TB-5	45.97	0.08	4.39
5	TB-10	52.55	0.11	5.19

calculated using the equation $\text{CI} = (I_{\text{max}} - I_{\text{back}})/I_{\text{max}} \times 100$, where I_{max} is the highest intensity value of TiO_2 (101), and I_{back} is the lowest intensity of PXRD pattern of catalyst. This gradual decline suggests that the introduction of Bi_2WO_6 slightly disrupted the structural order of TiO_2 , with the effect mainly confined to the near-surface region. Notably, no obvious peak shift was observed in the PXRD patterns ($<0.1^\circ$), indicating that the bulk crystal structure of TiO_2 remained essentially unchanged, without significant lattice reconstruction or the formation of a new crystalline phase. Therefore, the reduction in CI values is more reasonably attributed to local interfacial disorder and microstrain generated during heterojunction formation, rather than to a substantial change in lattice parameters. As the Bi_2WO_6 content increased, the interfacial contact area between the two phases became larger, leading to the gradual accumulation of surface stress in the TB-x samples. Such interfacial stress can reduce local crystallographic order without causing a measurable peak shift. These results further suggest

that the TB-x samples are not simple physical mixtures but rather heterostructures with effective interfacial coupling, and that the local lattice perturbation is mainly confined to the contact region. This moderate interfacial disturbance is expected to favor interfacial charge redistribution and internal electric field (IEF) formation, thereby facilitating charge transfer across the heterojunction [12].

Fig. 2d presents the FTIR spectra of pristine Bi_2WO_6 , bare TiO_2 , and the representative TB-5 heterojunction composite recorded over the range of 500–4000 cm^{-1} . All materials exhibit a broad, asymmetric absorption band centered at 3336 cm^{-1} , assigned to the stretching vibrations ($\nu(\text{O-H})$) of surface hydroxyl groups and physisorbed water molecules. The pronounced asymmetry of this envelope underscores extensive hydrogen-bonding networks, signaling a high surface density of -OH functionalities. This is corroborated by a complementary bending mode ($\delta(\text{O-H})$) at 1566 cm^{-1} from coordinated water. Retaining this rich surface hydroxylation post-thermal treatment is mechanistically vital; these -OH


domains serve a dual catalytic role as primary chemisorption sites for gaseous FA and as localized photogenerated hole-trapping centers that facilitate $\cdot\text{OH}$ radical evolution. Additionally, a minor feature at 1356 cm^{-1} is attributed to the stretching vibration ($\nu(\text{N-O})$) of trace residual nitrate/nitrite species originating from the hydrothermal precursors.

In the fingerprint region ($500\text{--}1000\text{ cm}^{-1}$), well-resolved bands correspond to characteristic metal-oxygen framework vibrations. These include Bi-O stretching in the layered $[\text{Bi}_2\text{O}_2]^{2+}$ units (600 cm^{-1}), bridging W-O-W and W-O-Bi stretching within the WO_6 octahedra ($600\text{--}850\text{ cm}^{-1}$) and overlapping Ti-O stretching Ti-O-Ti bridging modes of the anatase TiO_2 lattice. Notably, the TB-5 composite preserves all diagnostic absorption bands of both the Aurivillius-phase

Bi_2WO_6 and anatase TiO_2 matrices without discernible peak displacements or loss of diagnostic features. The absence of extraneous low-frequency features rules out the formation of bulk amorphous phases or secondary solid-state impurities at the interface, confirming that the chemical and crystalline integrity of both constituent semiconductors remains intact upon heterojunction assembly [30, 31].

To elucidate the surface chemical state of the TB-5 heterojunction catalyst, X-ray photoelectron spectroscopy (XPS) analysis was conducted with all binding energies (BE) calibrated against the C 1s reference at 284.80 eV . As presented in Fig. 3a, the Bi 4f XPS spectrum of Bi_2WO_6 exhibits two distinct peaks at 164.5 eV and 159.2 eV , corresponding to Bi $4f_{5/2}$ and Bi $4f_{7/2}$ states, respectively, while the TB-5

Fig. 3 XPS spectra of TB-5 along with the reference catalysts (Bi_2WO_6 and TiO_2): (a) Bi 4f, (b) Ti 2p, (c) W 4f, (d) O 1s, and (e) full XPS spectra

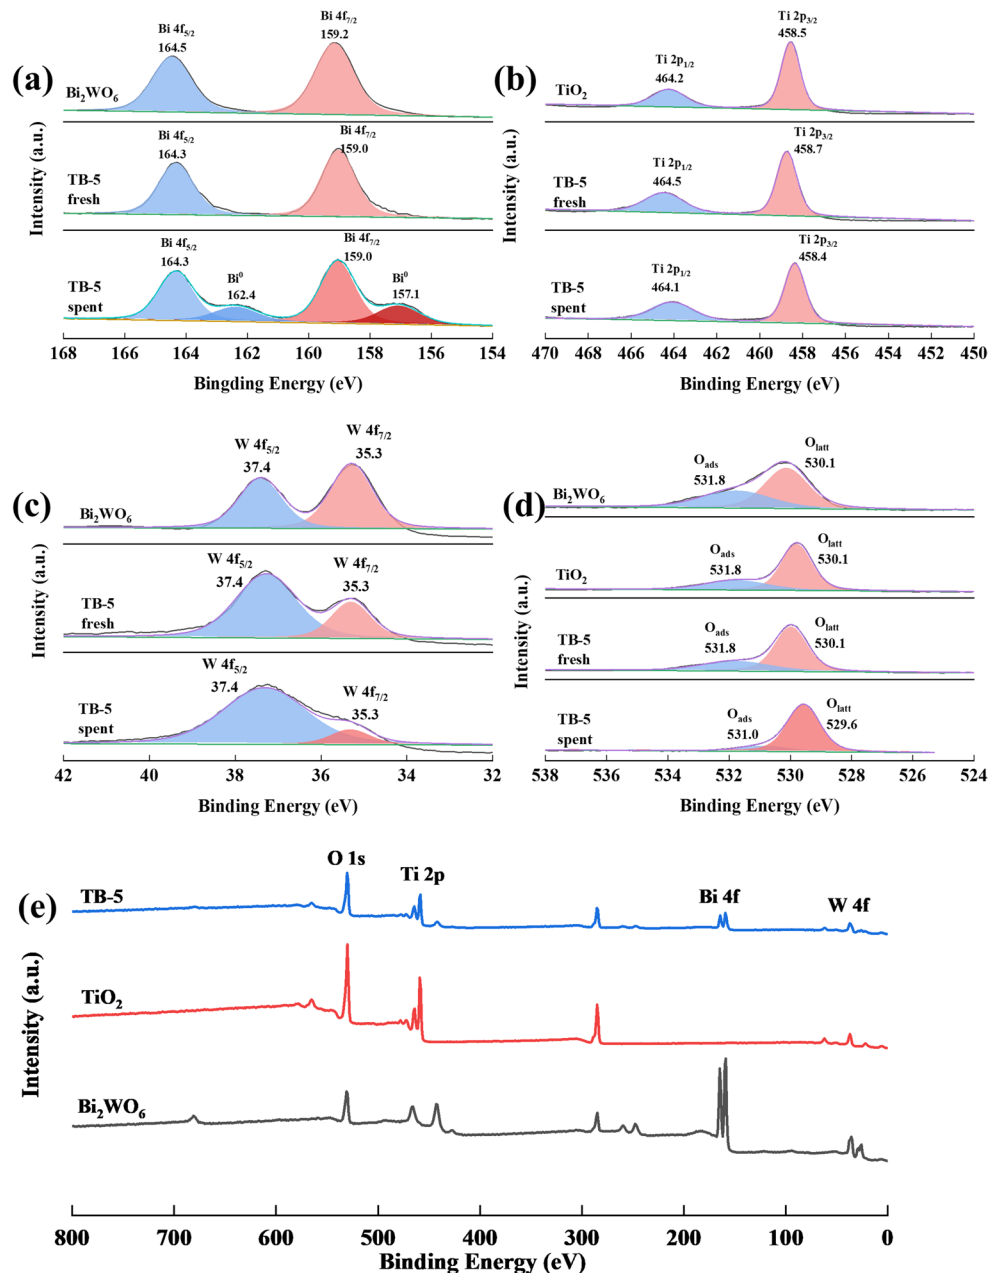

corresponding peaks shift to 164.3 and 159.0 eV [32]. This negative shift to lower binding energy indicates increased electron density around Bi species after heterojunction formation. In the case of pristine TiO_2 , as illustrated in Fig. 3b, Ti 2p spectra display characteristic peaks at 464.2 eV and 458.5 eV for Ti $2p_{1/2}$ and Ti $2p_{3/2}$ transitions. In contrast, the Ti 2p spectra of TB-5 exhibit these peaks at 464.5 eV and 458.7 eV, manifesting a positive shift of 0.2 eV compared to pure TiO_2 [13]. This positive shift to higher binding energy indicates electron depletion around Ti sites. Taken together, the opposite shifts of Bi 4f and Ti 2p support interfacial electron transfer from TiO_2 to Bi_2WO_6 upon heterojunction formation. This charge redistribution establishes an IEF directed from TiO_2 toward Bi_2WO_6 , driven by the equalization of Fermi levels across the interface [33]. The W 4f spectra of both Bi_2WO_6 and TB-5 presented in Fig. 3c show peaks at approximately 37.4 eV and 35.3 eV assigned to W $4f_{5/2}$ and W $4f_{7/2}$ states, with negligible shifts observed upon heterojunction formation, suggesting that the tungsten chemical state remains largely unchanged. Likewise, the O 1s spectra of pristine Bi_2WO_6 and TiO_2 materials (Fig. 3d) display a prominent peak at 531.8 eV corresponding to surface-adsorbed oxygen (O_{ads}) species without detectable shifts following composite formation (i.e., TB-5). The lattice oxygen (O_{latt}) peaks of Bi_2WO_6 , TiO_2 , and TB-5 appeared at 530.1, 529.9, and 530.0 eV, respectively [34]. The absence

of an obvious shift in the O_{ads} peak does not contradict the interfacial charge redistribution observed from Bi 4f and Ti 2p. This is because the broad components (including surface hydroxyls, adsorbed water, and weakly bound oxygen species) have an average binding energy that is less sensitive to localized interfacial electron transfer than the metal core levels. In comparison, the slight shift in lattice oxygen suggests that the oxygen environment is affected to a limited extent, while the dominant charge redistribution occurs mainly around the interfacial Bi and Ti sites. The survey spectra presented in Fig. 3e demonstrate that TB-5 contains the constituent elements Bi, W, Ti, and O, confirming successful integration of the Bi_2WO_6 and TiO_2 .

The UV-Vis DRS spectrum (Fig. 4a) shows that TiO_2 exhibits strong absorption in the ultraviolet range (≈ 200 – 363 nm) with a light absorption edge at ~ 310 nm. In contrast, Bi_2WO_6 absorbs strongly from ≈ 200 – 388 nm with a light absorption edge near ~ 330 nm, and its intensity extends further into the visible region. The electronic structures of the two materials differ significantly. TiO_2 possesses a large band gap, confining its light absorption to the ultraviolet spectrum [35]. In contrast, the VB of Bi_2WO_6 , formed by O 2p orbitals from the $[\text{BiO}]^+$ layers, lies at a higher energy, resulting in a narrower bandgap and a visible-light-responsive absorption edge [36]. Upon TB-x ($x=2, 5$, and 10) heterojunction materials, the light absorption edges shift

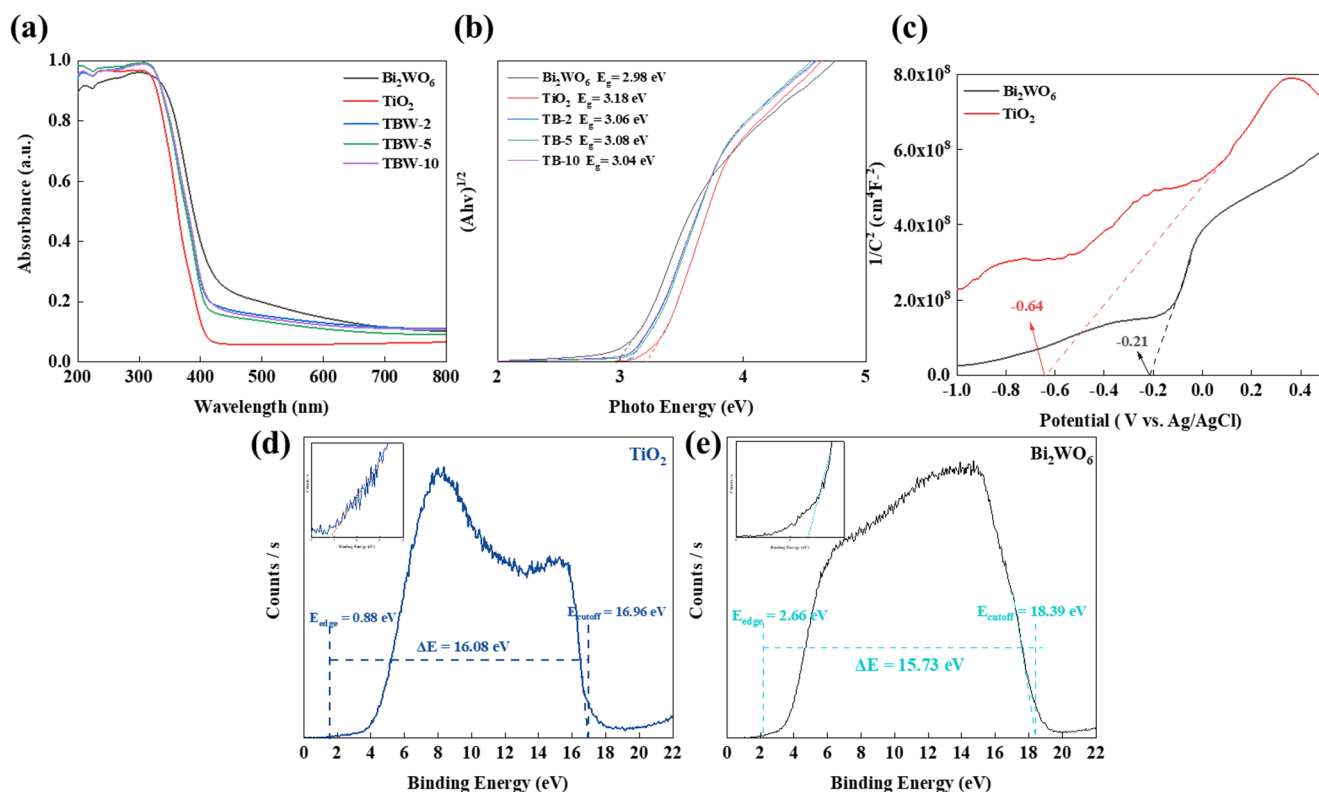


Fig. 4 Optoelectronic characterization of TB-x series catalysts along with the reference materials (Bi_2WO_6 and TiO_2). (a) UV-vis spectra, (b) Tauc plots, (c) Mott-Schottky curves, (d) UPS spectra of TiO_2 , and (e) UPS spectra of Bi_2WO_6

to longer wavelengths. Specifically, compared to pure TiO_2 , the light absorption edges for TB-2, TB-5, and TB-10 are red-shifted to approximately 315, 317, and 319 nm, respectively. This phenomenon is consistent with the alignment of Fermi-levels at the contact interface, which generates an IEF. The IEF creates band bending and interfacial charge-transfer states [37]. These factors collectively extend the spectral response and could increase the generation rate of electron-hole pairs. Correspondingly, the Tauc plots (Fig. 4b) indicate that the optical band gaps of TB-2, TB-5, and TB-10 are smaller than that of TiO_2 , reaching around 3.04, 3.06, and 3.08 eV, respectively.

Both Bi_2WO_6 and TiO_2 are confirmed as n-type semiconductors through the Mott-Schottky (M-S) curve analysis (Eq. 9, Fig. 4c), evidenced by the positive slopes of their respective $1/C^2$ versus potential plots [38]. This electronic structure characterization reveals a key distinction: TiO_2 's large bandgap confines its absorption to the ultraviolet spectrum, whereas the VB maximum in Bi_2WO_6 lies at a higher energy owing to O 2p orbitals. This results in a narrower bandgap and subsequent visible-light photoabsorption.

$$\frac{1}{C^2} = \frac{2}{\epsilon \times \epsilon_0 \times e \times N_d} \times (E - E_{FB} - \frac{KT}{e}) \quad (9)$$

Where C , ϵ , ϵ_0 , e , N_d , E , E_{FB} , K , and T represent the space charge capacitance ($\text{cm}^4 \text{F}^{-2}$), dielectric constant, vacuum dielectric constant ($8.86 \times 10^{-14} \text{ F/cm}$), donor density (cm^{-3}), applied potential (V Ag/AgCl), flat band potential (V Ag/AgCl), Boltzmann constant ($1.38 \times 10^{-23} \text{ J K}^{-1}$), and temperature (K) of n-type semiconductor, respectively [39]. The E_{FB} values of Bi_2WO_6 and TiO_2 were determined from

M-S analysis of EIS measurements to be -0.21 and -0.64 V vs. Ag/AgCl, respectively. Subsequently, the Nernst equation was used to convert these E_{FB} values into the normal hydrogen electrode (NHE) scale (Eq. 10).

$$E_{FB}(\text{NHE}) = E^\theta \left(\frac{\text{Ag}}{\text{AgCl}} \right) + E_{FB} \left(\frac{\text{Ag}}{\text{AgCl}} \right) + 0.059 \times pH \quad (10)$$

E^θ (Ag/AgCl) is 0.197 V. For n-type semiconductors, the E_{FB} is generally located at a potential ~ 0.2 eV more positive than the conduction band minimum (E_{CB}). Therefore, the E_{CB} positions of both Bi_2WO_6 and TiO_2 were calculated using the equation $E_{CB} = E_{FB}(\text{NHE}) - 0.2$, which are determined to be -0.213 V vs. NHE and -0.643 V vs. NHE, respectively. Finally, the valence band maximum (E_{VB}) positions were computed from the optical band gaps (E_g) and the calculated E_{CB} values via the relation $E_{VB} = E_g + E_{CB}$. Thus, the CB and VB positions of Bi_2WO_6 and TiO_2 are established as $-0.213/2.767$ V vs. NHE and $-0.643/2.537$ V vs. NHE, respectively (Fig. 5a).

The formation of ROS, particularly hydroxyl radicals ($\cdot\text{OH}$) and superoxide radicals ($\cdot\text{O}_2^-$), is critical, as these species are the primary oxidative agents responsible for the breakdown and ultimate mineralization of FA into CO_2 and H_2O . The $\cdot\text{OH}$ radical is known as one of the most powerful oxidizing agents in aqueous and surface chemistry. It attacks non-selectively, cleaving the C-H bonds of adsorbed FA and its intermediate species (e.g., dioxymethylene (DOM) and formate). Concurrently, the $\cdot\text{O}_2^-$ radicals contribute to the oxidative degradation chain and help suppress the recombination of photogenerated electron-hole pairs.

The potential for generating these ROS is directly governed by the semiconductor's band structure (Fig. 5a). For

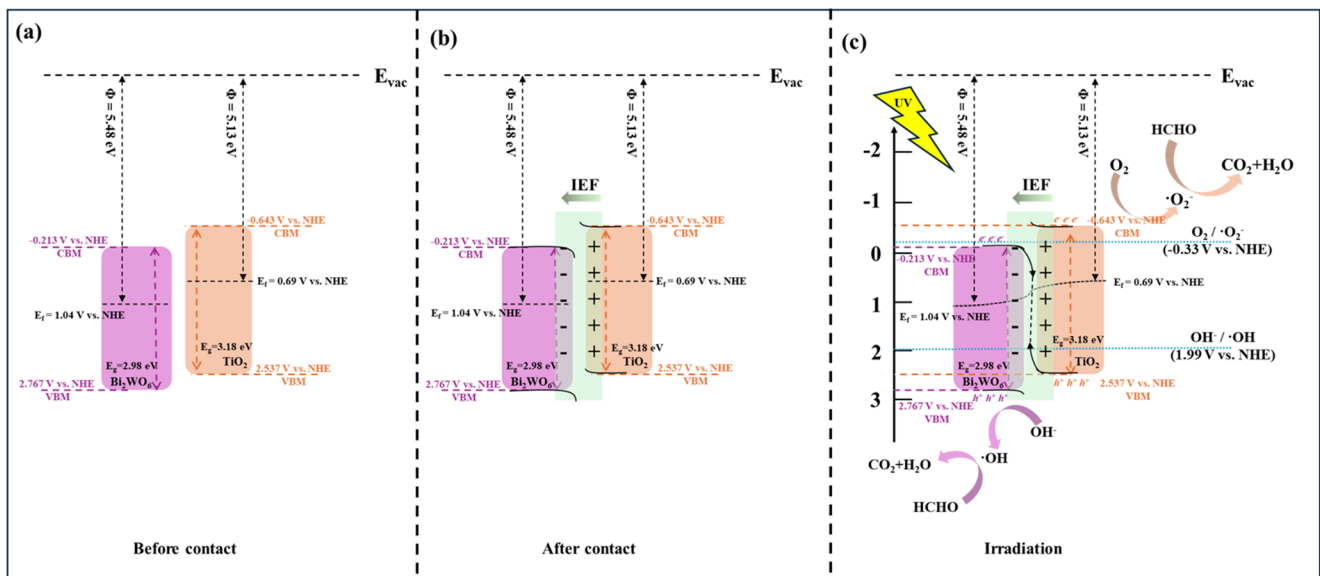


Fig. 5 Plot of S-scheme heterojunction and the associated charge transfer mechanism between Bi_2WO_6 (as OP) and TiO_2 (as RP): (a) before contact and (b-c) after contact [under (b) dark and (c) light irradiation conditions]

the efficient production of surface-bound $\cdot\text{OH}$ radicals, which is crucial for gas-phase photocatalysis, the VB potential must be sufficiently positive to oxidize surface hydroxyl groups ($-\text{OH}$) or adsorbed water (H_2O). This is quantified by the thermodynamic requirement that the VB potential must be more positive than the standard oxidation potential of $\text{H}_2\text{O}/\cdot\text{OH}$ (+2.72 to 2.99 V vs. NHE) or, more practically for surface-adsorbed species, $\text{OH}^-/\cdot\text{OH}$ (+1.99 V vs. NHE). Therefore, a key material property for efficient gas-phase $\cdot\text{OH}$ radical generation is VB potential significantly more positive than +2.0 V vs. NHE. This energetic configuration enables the photogenerated holes (h^+) to oxidize ubiquitous surface-adsorbed hydroxyl ions (OH^-) into gaseous $\cdot\text{OH}$ radicals. These radicals then diffuse from the catalyst surface to initiate the oxidative degradation of FA molecules in the adjacent gas phase, making this interfacial $\cdot\text{OH}$ shuttle a critical step for the PCO of air pollutants.

The work function difference ($\Delta\Phi$) is a critical parameter for offering valuable insights into the interfacial charge transfer mechanism in heterojunction catalysts. The $\Delta\Phi$ values of Bi_2WO_6 and TiO_2 were determined experimentally using UPS.

$$\Delta\Phi = h\nu - (E_{\text{cutoff}} - E_{\text{edge}}) \quad (11)$$

where $h\nu$ represents the incident photon energy (21.22 eV). The secondary electron cutoff energy (E_{cutoff}) and the Fermi edge (E_{edge}) of Bi_2WO_6 (18.39/2.66 eV) and TiO_2 (16.96/0.88 eV) were determined from the UPS spectra (Fig. 4d-e), the $\Delta\Phi$ values of Bi_2WO_6 and TiO_2 can be determined as 5.48 eV and 5.13 eV based on Eq. 11, respectively. Furthermore, the Fermi levels (E_F) relative to the NHE of Bi_2WO_6 and TiO_2 were computed as 1.04 V vs. NHE and 0.69 V vs. NHE, respectively, according to the equation, $\text{NHE} = \Delta\Phi - 4.44$. Before the two types of semiconductors contact, the Fermi level of each semiconductor remains independent, and the band positions are determined solely by their intrinsic electronic structures (Fig. 5a). After contacting under equilibrium conditions, this energy alignment drives electron transfer at the interface, inducing upward band bending (electron depletion) in TiO_2 and downward band bending (electron accumulation) in Bi_2WO_6 . Consequently, an IEF directed from TiO_2 to Bi_2WO_6 is established across the TB-5 heterojunction catalysts (Fig. 5b) [40]. The charge transfer pathway in the TB-5 heterojunction is conclusively determined by its electronic structure, so that the staggered band alignment of TB-5 could theoretically support a type II or an S-scheme heterojunction [41, 42]. However, the key distinction lies in the fate of the photogenerated charge carriers. In a type-II heterojunction, e^- in the CB of Bi_2WO_6 transfer to the CB of TiO_2 , while h^+ in the VB of TiO_2 migrate to the VB of Bi_2WO_6 . This pathway


promotes spatial charge separation but weakens the overall redox ability. By contrast, in the S-scheme pathway, the IEF and Coulombic attraction drive the recombination of low-energy e^- in the CB of Bi_2WO_6 with low-energy h^+ in the VB of TiO_2 . As a result, high-energy e^- and h^+ remain in the CB of TiO_2 and in the VB of Bi_2WO_6 , respectively. This charge-transfer route preserves the strong reduction and oxidation capacities required for ROS generation and FA mineralization. Thus, despite the staggered band alignment, TB-5 retains an S-scheme mechanism (rather than forming a type-II heterojunction), as evidenced by the work function difference, interfacial band bending, and retention of strong redox potentials [13] (Fig. 6c).

To rigorously evaluate the real-time spatial migration of photogenerated charge carriers across the heterojunction interface, in-situ XPS was executed under alternating UV-off and UV-on conditions (Fig. 6). Upon UV illumination, the characteristic core levels of the TiO_2 reduction photocatalyst (Ti 2p_{3/2} and Ti 2p_{1/2}) shift toward lower BEs by ΔBE 0.4 eV (from 458.7 to 464.5 eV to 458.3 and 464.1 eV, respectively). This negative displacement provides definitive evidence of localized photoelectron accumulation within the CBM of TiO_2 , corroborating its role as the electron-accepting component (RP) in the step-scheme pathway. Concurrently, the core-level signals of the Bi_2WO_6 oxidation photocatalyst (Bi 4f_{7/2}, Bi 4f_{5/2}, W 4f_{7/2}, and W 4f_{5/2}) also shifted toward lower BEs ($\Delta\text{BE} = -0.2$ to -0.4 eV).

In an idealized S-scheme pathway, the oxidation photocatalyst is expected to display an upward electrostatic binding energy shift due to localized electron depletion. However, this anomalous downward shift of Bi_2WO_6 signals is directly rationalized by the simultaneous emergence of two new peaks at 156.8 and 162.1 eV, indicative of zero-valent metallic bismuth (Bi^0). This behavior uncovers a competitive, light-driven surface restructuring process wherein a fraction of the photoexcited electrons drives the partial in-situ photoreduction of lattice Bi^{3+} ions to metallic Bi^0 . The higher electron density of the reduced Bi^0 species, coupled with the superior extra-atomic electronic screening capacity of the newly formed metallic domains, induces a dominant downward chemical and relaxation shift that successfully overrides the expected S-scheme electrostatic upward shift. Ultimately, the in-situ evolved metallic Bi^0 centers serve an integrated, dual-functional role: they act as a highly conductive conduit that works in tandem with the S-scheme internal electric field to fast-track carrier extraction, while concurrently introducing localized surface plasmon resonance properties that expand visible-light harvesting capabilities.


In addition, the generation of ROS species from TB-5 under UV on/off conditions were evaluated using EPR spectroscopy (Fig. 7a). The absence of signals corresponding to

Fig. 6 In-situ XPS spectra of TB-5 under UV on/off conditions: (a) Bi 4f, (b) Ti 2p, (c) W 4f, and (d) O 1s

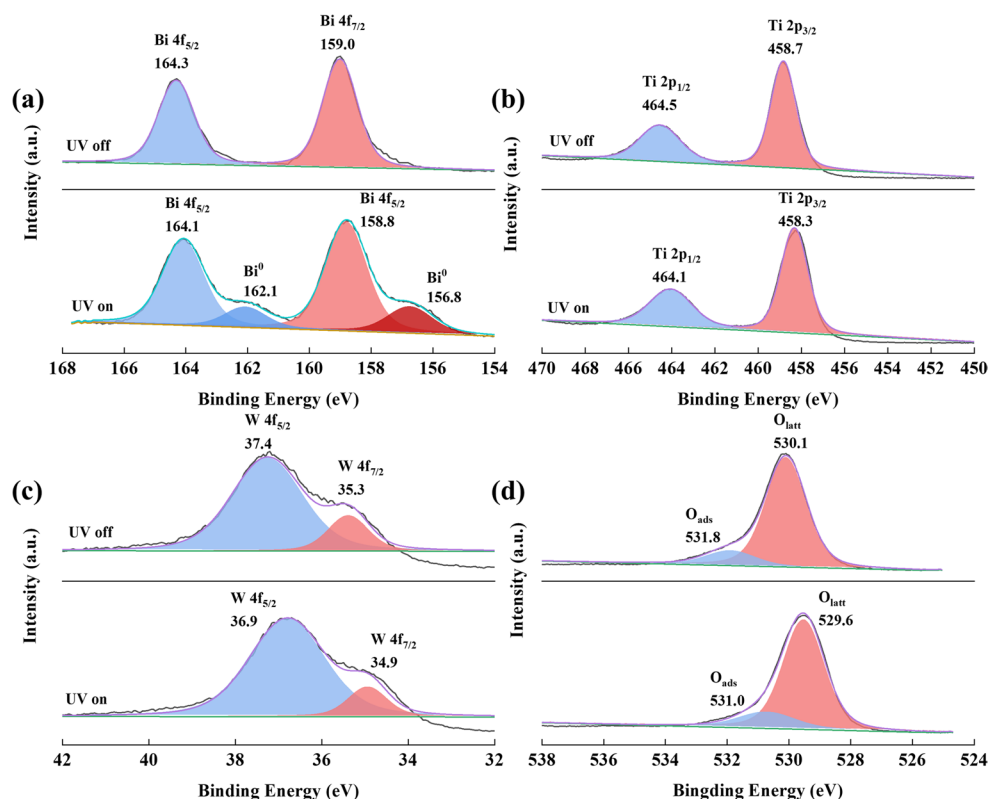

$\cdot\text{O}_2^-$ and $\cdot\text{OH}$ under dark conditions indicates that no ROS were generated during the adsorption process. In contrast, after 5 min of UV irradiation, the EPR spectra of TB-5 exhibited 6 characteristic peaks of $\cdot\text{O}_2^-$ at 3476.2, 3484.2, 3489.5, 3498.0, 3503.7, and 3511.7 G and four characteristic peaks of $\cdot\text{OH}$ at 3474.0, 3488.1, 3503.2, and 3518.1 G. These results demonstrate that $\cdot\text{O}_2^-$ and $\cdot\text{OH}$ are generated by TB-5 under UV light, which can effectively promote the degradation of FA [43].

To identify the dominant reactive oxygen species involved in FA degradation, radical-quenching experiments were conducted by introducing specific scavengers into the photocatalytic system. p-Benzoquinone (BQ) and isopropanol (IPA) were employed as selective scavengers for $\cdot\text{O}_2^-$ and $\cdot\text{OH}$, respectively, based on the following scavenging reactions [44]:




To elucidate the primary oxidation pathways and quantify the individual contributions of key reactive oxygen species (ROS), photocatalytic FA degradation evaluations were performed over the TB-5 heterojunction using selective radical scavenging agents (Fig. S2). Under unperturbed conditions, TB-5 achieved quantitative FA conversion (X_{FA} of 100%)

within 600 s, corresponding to a CADR of 10.37 L min^{-1} . The introduction of IPA and BQ significantly suppressed steady-state activity; at 600 s, X_{FA} dropped to 64.50% and 71.72%, respectively. Concurrently, the CADR dropped to 2.22 L min^{-1} (under IPA) and 3.34 L min^{-1} (under BQ). These kinetic interruptions demonstrate that both OH and $\cdot\text{O}_2^-$ radicals function as vital driving forces during the FA PCO process. Crucially, the more pronounced decline in CADR induced by IPA sequestration dictates that while both ROS are active, the $\cdot\text{OH}$ -mediated pathway exerts a dominant kinetic influence on the interfacial destruction of FA molecules over the S-scheme architecture.

Electrochemical analysis, such as EIS and PC, effectively evaluates conductivity and charge transfer [45]. As shown in Fig. 7b, TB-5 has the lowest charge transfer resistance (3.35Ω), which is 1.97 to 0.31 times lower than the other ones. Consistently, the PC of TB-5 is the highest ($86 \mu\text{A cm}^{-2}$), which is 4.30 to 1.15 times higher than Bi_2WO_6 , TiO_2 , TB-2, and TB-10, respectively (Fig. 7c). This demonstrates that TB-5 has superior charge separation and light responsiveness, resulting in excellent photocatalytic performance [46]. The charge separation efficiency was further confirmed by PL spectroscopy (Fig. 7d). A lower PL intensity signifies suppressed electron-hole recombination, as the emission stems from charge carrier recombination [47]. In contrast, the reduced PL intensity of TB-x compared with pure TiO_2 reflects carrier-recombination processes modulated by the

Fig. 7 Photoelectrochemical properties of the TB-x series catalysts along with the reference materials (Bi_2WO_6 and TiO_2): (a) EPR spectra of TB-5, (b) EIS spectra, (c) Transient PC response under UV on/off cycles, and (d) PL spectra

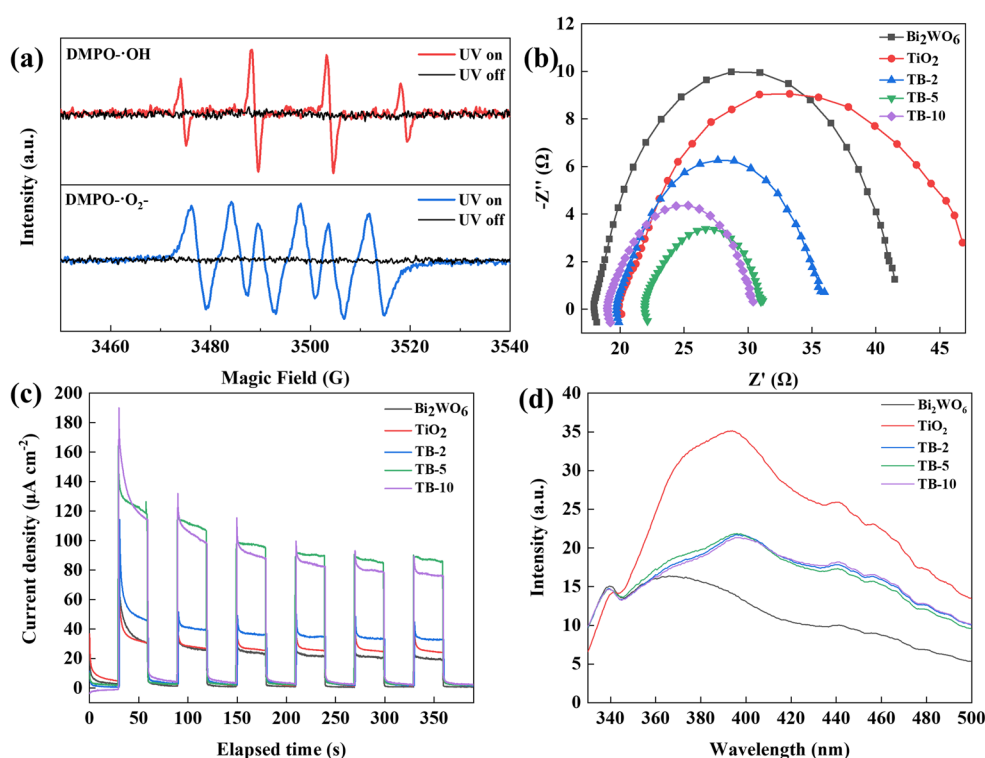

heterojunction interface [48]. Among the heterojunction catalysts, TB-5 exhibited the PL intensity, aligning with the EIS and PC results and affirming its excellent charge separation capability.


3.2 FA removal performance of TB-x photocatalysts and parameter-dependent behavior of TB-5

The photocatalytic performance evaluation results demonstrate that TB-x composite photocatalysts exhibit significantly superior FA degradation efficiency compared to TiO_2 . Fig. 8a illustrates the temporal relationship between the X_{FA} and the tested photocatalysts' performance. Under 360 s of illumination, the X_{FA} of TB-x photocatalysts displayed the order of: TB-5 (93.6%) > TB-10 (92.0%) > TB-2 (82.2%) > TiO_2 (76.9%) > Bi_2WO_6 (56.6%) (Fig. 8a). This contrasts greatly with UV off condition in which Bi_2WO_6 shows the maximum X_{FA} (39.5%). When the reaction time is extended to 780 s, the TB-x composite photocatalysts achieved complete mineralization of FA ($X_{\text{FA}} = 100\%$), while TiO_2 and Bi_2WO_6 only reached 98.7 and 56.6%, respectively. Among them, TB-5 demonstrated the best FA removal performance, with a SCADR of $123.80 \text{ L min}^{-1} \text{ g}^{-1}$, which is 1.9 times better than TiO_2 ($59.51 \text{ L min}^{-1} \text{ g}^{-1}$) and 3.5 times better than Bi_2WO_6 ($32.25 \text{ L min}^{-1} \text{ g}^{-1}$) (Table 2). Furthermore, TB-5 also showed the highest r_{10} , r_{max} , AQY, and MAQY value of $1.72 \text{ mmol g}^{-1} \text{ h}^{-1}$, $0.35 \text{ mmol g}^{-1} \text{ h}^{-1}$, 2.68E-01%, and $3.20\text{E-}02 \text{ molecules photon}^{-1} \text{ g}^{-1}$, which is 1.5, 1.6, 1.3, and 1.6 times better than TiO_2 and 2.3, 2.7, 2.3, 2.6 times

better than Bi_2WO_6 . Overall, all performance indicators confirmed that TB-5 is the most effective catalyst for FA degradation. Therefore, our study selects TB-5 as the optimal photocatalyst for a subsequent systematic investigation of the influence of various process parameters on FA degradation. It should be noted that the higher AQY and reaction rates observed at 5 ppm reflect a higher instantaneous utilization of active sites and photogenerated charge carriers under emission-level conditions, rather than a loss of practical applicability at lower concentrations. At lower FA levels, the absolute reaction rate and photon utilization decrease because fewer FA molecules are available to occupy surface active sites. Nonetheless, the catalyst can still achieve rapid purification owing to the lower pollutant burden, as reflected by the higher CADR/SCADR values obtained at 1 ppm. In this sense, the concentration dependence indicates a shift in the dominant performance metric: rate-based and quantum-yield descriptors are maximized at higher FA concentrations, whereas air-cleaning efficiency is enhanced more favorably at lower concentrations.

To establish a baseline for mass balance and decouple non-catalytic FA loss from true photocatalytic degradation, a control experiment was conducted under identical illumination and experimental conditions in the absence of a photocatalyst (Fig. S3). Throughout the 600 s reaction profile, the X_{FA} remained negligible, peaking at a marginal 4.34% at the terminal sampling point. This minor attenuation confirms that parallel abiotic pathways, such as homogenous photolysis, system/filter adsorption, exert a statistically

Fig. 8 Comparison of PCO efficiency (X_{FA}) of TB-x photocatalysts (base conditions: FA=5 ppm, m_{cat} =100 mg, flow rate=160 L min⁻¹, RH=0%, and O₂ concentration=21 vol%): (a) all photocatalysts prepared in this study, (b–g) tests under control of each process variable ((b) RH, (c) m_{cat} , (d) FA concentration, (e) AP flow rate, (f) O₂ concentration, (g) hydrothermal duration (6, 15, and 48 h)), and (h) tests over five cycles

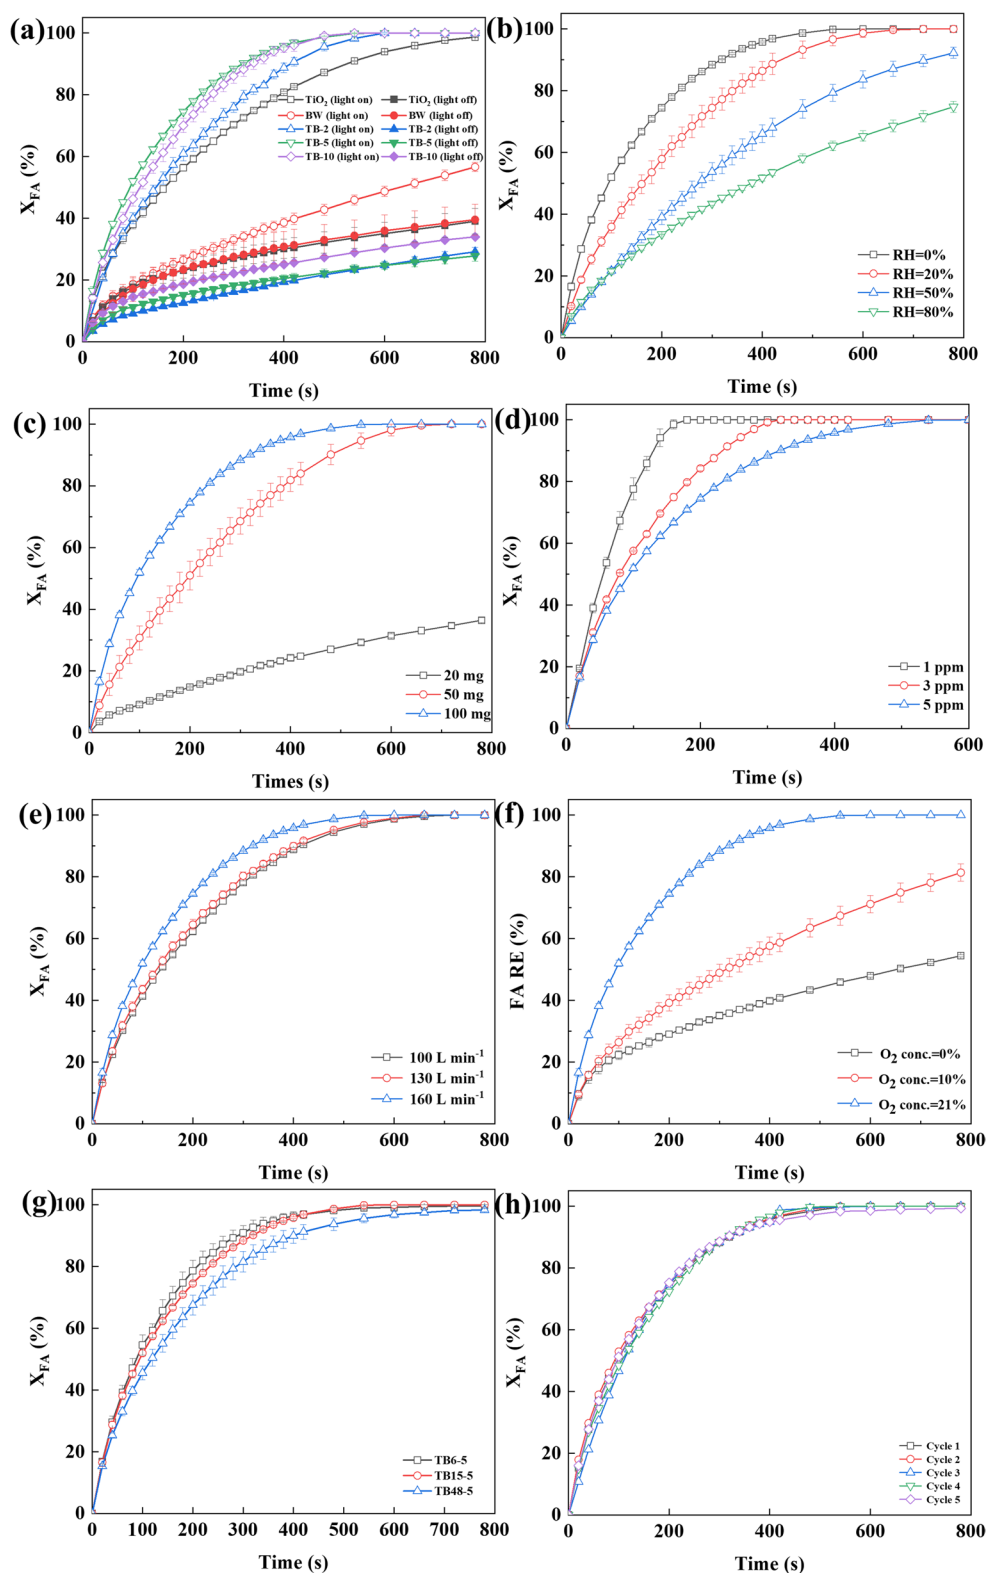

insignificant influence on FA concentrations under the prevailing operational matrix. Consequently, the rapid, high-efficiency FA removal observed in the catalyst-loaded systems can be unambiguously assigned to an interfacial

photocatalytic oxidation mechanism driven by the active heterojunction.

The presence of relative humidity (RH) significantly influences the photocatalytic performance of catalysts,

Table 2 Comparison of FA photocatalytic oxidation performance of TB-x series catalysts along with the Bi₂WO₆ and TiO₂ under varied operating parameters within 13 min

Order	Material	Light condition	X _{FA} (%)	RH (%)	Mass g	FA conc. ppm	Flow rate L min ⁻¹	O ₂ conc. (%)	Synthesis time (hour)	CADR L min ⁻¹	SCADR L min ⁻¹	r ₁₀ mmol g ⁻¹ h ⁻¹	r _{max} mmol g ⁻¹ h ⁻¹	AQY %	MAQY molecules photon ⁻¹ g ⁻¹
(a) Photocatalyst															
1	Bi ₂ WO ₆	Light on	56.6	0	0.096	5	160	21	15	3.11	32.25	0.58	0.13	1.17E-01	1.21E-02
2	TiO ₂		98.7		0.100					5.73	59.51	1.11	0.22	2.04E-01	2.04E-02
3	TB-2		100		0.094					6.50	69.17	0.95	0.28	2.44E-01	2.60E-02
4	TB-5		100		0.084					10.37	123.80	1.72	0.35	2.68E-01	3.20E-02
5	TB-10		100		0.097					9.33	96.66	1.35	0.30	2.68E-01	2.78E-02
6	Bi ₂ WO ₆	Light off	39.5		0.096					2.01	22.34	0.41	0.09	-	-
7	TiO ₂		39		0.100					1.98	20.56	0.51	0.09	-	-
8	TB-2		29.1		0.094					1.04	11.07	0.16	0.07	-	-
9	TB-5		27.8		0.084					1.40	14.85	0.28	0.07	-	-
10	TB-10		34		0.097					1.75	18.12	0.38	0.08	-	-
(b) RH															
11	TB-5	Light on	100	0	0.084	5	160	21	15	10.37	123.80	1.77	0.35	2.68E-01	3.20E-02
12			100	20						6.15	73.35	1.06	0.29	2.24E-01	2.67E-02
13			92.3	50						3.38	40.36	0.63	0.25	1.91E-01	2.27E-02
14			74.8	80						2.33	27.76	0.53	0.20	1.54E-01	1.84E-02
(c) Mass loading															
15	TB-5	Light on	36.47	0	0.022	5	160	21	15	0.71	32.40	0.71	0.10	7.54E-02	3.44E-02
16			100		0.046					5.31	115.24	1.64	0.29	2.24E-01	4.85E-02
17			100		0.084					10.37	123.80	1.77	0.35	2.68E-01	3.20E-02
(d) FA conc.															
18	TB-5	Light on	100	0	0.084	1	160	21	15	21.09	251.65	0.41	0.23	1.79E-01	2.13E-02
19			100		3					11.94	142.51	1.12	0.37	2.68E-01	3.20E-02
20			100		5					10.37	123.80	1.77	0.35	2.68E-01	3.20E-02
(e) Flow rate															
21	TB-5	Light on	100	0	0.084	5	100	21	15	7.04	84.01	1.42	0.29	2.24E-01	2.67E-02
22			100				130			7.42	88.56	1.37	0.32	2.44E-01	2.91E-02
23			100				160			10.37	123.80	1.77	0.35	2.68E-01	3.20E-02
(f) O ₂ conc.															
24	TB-5	Light on	54.44	0	0.084	5	160	0	15	2.44	29.14	0.95	0.15	1.12E-01	1.34E-02
25			81.37					10		3.30	39.43	1.14	0.22	1.68E-01	2.01E-02
26			100.00					21		10.37	123.80	1.77	0.35	2.68E-01	3.20E-02
(g) Different hydrothermal time															
27		Light on	99.7	0	0.099	5	160	21	6	11.05	110.74	1.55	0.23	2.06E-01	2.08E-02
28	TB-5		100		0.084				15	10.37	123.80	1.77	0.35	2.68E-01	3.20E-02
29			98.3		0.073				48	7.79	107.34	1.75	0.31	2.03E-01	2.80E-02

Table 2 (continued)

Order	Material	Light condition	X _{FA} (%)	RH (%)	Mass g	FA conc. ppm	Flow rate L min ⁻¹	O ₂ conc. (%)	Synthesis time (hour)	CADR L min ⁻¹ g ⁻¹	SCADR L min ⁻¹ g ⁻¹	r ₁₀ mmol g ⁻¹ h ⁻¹	r _{max} mmol g ⁻¹ h ⁻¹	AQY %	MAQY molecule photon ⁻¹ g ⁻¹
(h) Reusability															
30	TB-5	Light on	100	0	0.084	5	160	21	15	10.63	126.85	1.80	0.35	2.68E-01	3.20E-02
31			100							10.51	125.45	1.72	0.39	2.98E-01	3.56E-02
32			100							9.99	119.26	1.09	0.35	2.68E-01	3.20E-02
33			100							10.31	123.05	1.52	0.39	2.98E-01	3.56E-02
34			100							10.21	121.91	1.62	0.27	2.06E-01	2.46E-02

while its catalytic oxidation mechanism for VOCs is relatively complex [49]. As shown in Fig. 8b, increasing environmental RH levels significantly reduced the X_{FA} of TB-5. At 600 s, X_{FA} showed a decreasing trend of: 0% RH (100%) > 20% RH (98.63%) > 50% RH (83.67%) > 80% RH (74.80%). Specifically, the CADR/SCADR also exhibited a clearly decreasing trend with increasing RH: 0% RH (10.37 L min⁻¹/123.80 L min⁻¹ g⁻¹) > 20% RH (6.15 L min⁻¹/73.35 L min⁻¹ g⁻¹) > 50% RH (3.38 L min⁻¹/40.36 L min⁻¹ g⁻¹) > 80% RH (2.33 L min⁻¹/27.76 L min⁻¹ g⁻¹) (Table 2). Similarly, r₁₀, r_{max}, AQY, and MAQY values showed the same trend with X_{FA}. Specifically, the r₁₀/MAQY values (1.77 mmol g⁻¹ h⁻¹/3.20E-02 molecule photon⁻¹ g⁻¹) of TB-5 at 0% RH were approximately 0.7/0.2, 1.8/0.4, and 2.3/0.7 times higher than those of the 20, 50, and 80% RH, respectively. This phenomenon can be explained by the competitive relationship between FA molecules and H₂O on the surface of TB-5 [50]. In a humid environment, H₂O molecules may form a thin water film on the surface of TB-5, blocking active sites and inhibiting FA mineralization [51].

Furthermore, this study systematically investigated the effects of catalyst mass (20–100 mg) and initial FA concentration (1–5 ppm) on the FA removal performance of TB-5. As shown in Fig. 8c, the X_{FA} of TB-5 significantly improved with an increasing catalyst mass. At 600 s, X_{FA} of TB-5 with different mass shows a trend of: 100 mg (100%) > 50 mg (98.1%) > 20 mg (31.41%). TB-5 exhibited the best performance under 100 mg mass loading, with a CADR value, SCADR value, and AQY value reaching 10.37 L min⁻¹, 123.80 L min⁻¹ g⁻¹, and 2.68E-01%, respectively. Additionally, the MAQY value (i.e., 4.85E-02 molecule photon⁻¹ g⁻¹) of TB-5 with 50 mg was 1.4 times that of 20 mg and 1.5 times that of 100 mg, respectively (Table 2). This can be attributed to the higher catalyst mass providing more active sites, thereby promoting FA removal (Hua et al., 2024).

The effect of initial FA concentration on the performance of TB-5 is also plotted in Fig. 8d. Within 600 s, TB-5 could achieve complete degradation of FA (X_{FA}=100%) across various initial FA concentrations (1–5 ppm). This study found that the CADR and SCADR values decreased with increasing FA concentration, showing the following trend: 1 ppm (21.09 L min⁻¹/251.65 L min⁻¹ g⁻¹) > 3 ppm (11.94 L min⁻¹/142.51 L min⁻¹ g⁻¹) > 5 ppm (10.37 L min⁻¹/123.80 L min⁻¹ g⁻¹). However, the r₁₀, AQY, and MAQY values exhibited an opposite trend: 1 ppm (0.41 mmol g⁻¹ h⁻¹/1.79E-01%/2.13E-02 molecule photon⁻¹ g⁻¹) < 3 ppm (1.12 mmol g⁻¹ h⁻¹/2.68E-01%/3.20E-02 molecule photon⁻¹ g⁻¹) < 5 ppm (1.77 mmol g⁻¹ h⁻¹/2.68E-01%/3.20E-02 molecule photon⁻¹ g⁻¹). The observed trends occur because CADR/SCADR and r₁₀/AQY/MAQY measure different aspects of performance. The system is most efficient at cleaning air (high CADR) at low concentrations because

the fixed number of active sites on the catalyst can rapidly reduce a dilute pollutant level to zero. Conversely, it is most active and utilizes light best (high r_{10} , AQY, MAQY) at high concentrations because the abundant FA molecules ensure the catalyst's active sites are constantly occupied and working at their maximum capacity. This higher reactant concentration drives a greater absolute number of degradation events per unit time and improves the quantum yield by out-competing inherent electron-hole recombination [9].

The influence of key operational parameters on the photocatalytic performance of the optimal TB-5 catalyst was also investigated in terms of flow rate, O_2 levels, and synthesis conditions. As illustrated in Fig. 8e and summarized in Table 2, an increase in the air purification flow rate from 100 to 160 L min⁻¹ led to a consistent enhancement in all performance metrics, including X_{FA} , SCADR, and r_{10}/r_{max} . This uniform improvement is attributed to enhanced mass transfer in the AP system with continuous recirculation of feed gas, which facilitates faster contact between FA molecules and the catalyst's active sites [52]. Similarly, the concentration of O_2 was found to be critically important, as demonstrated in Fig. 8f; Table 2. All evaluated metrics, X_{FA} , SCADR, r_{10} , r_{max} , and MAQY, exhibited a strong, positive correlation with increasing O_2 concentration. This clear trend underscores the essential role of molecular oxygen as a primary electron scavenger for the generation of ROS, such as $\cdot O_2^-$, which are vital for the oxidative degradation of FA [53]. In contrast to the uniform trends observed for flow rate and O_2 , the effect of hydrothermal synthesis duration (6, 15, and 48 h) on the TB-5 series revealed a more complex relationship, as shown in Fig. 8g; Table 2. The X_{FA} and specific activity metrics (SCADR and AQY) were maximized for the material prepared with an intermediate duration, TB-5, indicating that this condition achieves an optimal balance between the crystallinity of Bi_2WO_6 and the phase composition of TiO_2 for effective S-scheme charge transfer [54, 55]. Interestingly, the CADR results followed a different trend as TB-5 prepared over 6 h (i.e., the shortest synthesis duration) exhibited the highest value (Table 2). This divergence highlights a nuanced trade-off, where insufficient crystallization time may yield a high initial surface area but compromises the electronic interaction crucial for long-term heterojunction stability and quantum efficiency.

3.3 Reusability of photocatalyst and FA mineralization

To evaluate the stability of TB-5, FA PCO experiments were repeated five times using 5 ppm FA. After 5 cycles (each cycle over 13 min), TB-5 was still able to achieve 100% of X_{FA} . Moreover, there is no significant decline in the values of CADR, SCADR, r_{10} , r_{max} , AQY, and MAQY

(Table 2), indicating that TB-5 possesses excellent stability and potential for practical applications. The photocatalytic mineralization performance of TB-5 toward FA vapor was also assessed by monitoring CO_2 evolution (Fig. S4). Under UV irradiation at 0% RH, in a single run with an initial FA concentration of 100 ppm for 120 min, X_{FA} of TB-5 could reach 96.6% while Y_{CO_2} attained 81.6%. These results demonstrate that TB-5 exhibits high degradation activity and mineralization capability toward FA.

Post reaction XPS analysis of TB-5 heterojunction provides concrete evidence for the S-scheme charge-transfer pathway and uncovers the surface chemical evolution occurring during photocatalytic FA oxidation (Fig. 3). In the post-catalytic Bi 4f spectrum, the primary Bi^{3+} doublet ($Bi\ 4f_{7/2}$ and $Bi\ 4f_{5/2}$) remains fixed at its initial BE positions, confirming that the bulk chemical environment of the Bi_2WO_6 lattice is well-preserved. However, the persistent presence of the fitted metallic doublet (Bi^0) at 157.0 and 162.3 eV validates the permanent in-situ photoreduction of surface-localized Bi^{3+} sites by accumulated interfacial electrons. Because the bulk Bi^{3+} framework remains electrostatically unperturbed, this reduction is clearly restricted to the outermost surface coordinates and does not trigger bulk phase transformations, verifying a highly localized interfacial electron-trapping event. Concurrently, the W 4f core levels do not exhibit any detectable shifts post-reaction. This total invariance demonstrates the robust chemical stability of the structural WO_6 polyhedral framework against anodic photocorrosion, ensuring that photogenerated holes are selectively channeled into external FA oxidation rather than lattice degradation.

Conversely, the post-reaction Ti 2p and O 1s core levels maintain a distinct negative shift toward lower BEs. This permanent displacement reflects a state of steady-state electron enrichment within the TiO_2 RP throughout the continuous photocatalytic cycle. Mechanistically, the high-binding-energy O 1s component at 531.0 eV, assigned to chemisorbed oxygen and surface hydroxyl species (O_{ads}), undergoes a notable contraction in peak area post-reaction. This depletion provides direct spectroscopic proof of the dynamic activation and consumption of surface -OH groups to generate reactive $\cdot OH$ radicals, which subsequently drive the interfacial chemical destruction of FA.

Complementary FTIR analysis of the fresh and spent heterojunctions supports these structural and surface insights (Fig. 2d). The spent TB-5 photocatalyst largely retains the characteristic lattice vibrational bands of the fresh sample in the low-wavenumber region (500–1000 cm⁻¹), which correspond to Bi-O, W-O/W-O-W, and Ti-O/Ti-O-Ti modes. This confirms that the primary Bi_2WO_6 and TiO_2 oxide frameworks remain intact, ruling out bulk lattice decomposition. Conversely, the hydroxyl-related features attenuate

significantly in the spent material, most notably the broad $\nu(\text{O-H})$ stretching envelope at 3336 cm^{-1} and the bending $\delta(\text{O-H})$ band at 1566 cm^{-1} . This attenuation indicates the consumption or restructuring of surface hydroxyls and co-adsorbed water during photocatalysis. These surface species act as primary adsorption sites and sacrificial precursors for $\cdot\text{OH}$ radical generation. The fact that their depletion directly tracks the O 1s XPS trends confirms their active participation in the FA oxidation pathway.

3.4 Photocatalytic FA oxidation pathway and mechanism


3.4.1 In-situ DRIFTS

To reveal the specific reaction pathway of FA degradation by TB-5, we performed the in-situ DRIFTS analysis (Fig. 9). The spectral evolution under different conditions provides critical kinetic insights into the surface reaction mechanism. Initial adsorption under dry and dark conditions is shown in Fig. 9a. The interaction of FA molecules with the TB-5 surface facilitated the formation of DOM, as confirmed by a peak at 1114 and 1268 cm^{-1} . Peaks at 1721 cm^{-1} (C=O stretching vibration of FA) was also observed [56]. The rapid formation of DOM in the dark indicates strong chemisorption even without photo-activation. Moreover, the negative band near 3570 cm^{-1} indicates the loss of pre-existing

surface-bridging hydroxyl groups ($-\text{OH}$) relative to the hydrated background spectrum. During the subsequent dry purge, these $-\text{OH}$ species are consumed, leading to a decrease in their absorbance. The spectral changes confirm that the highly reactive TB-5 surface drives the transformation of DOM into HCOO^- species.

The spectral evolution provides critical kinetic insights into the surface reaction. The initial rapid formation of DOM in the dark (Fig. 9a) suggests strong chemisorption and interaction of FA with the catalyst surface, even without photo-activation. Upon UV irradiation (Fig. 9b), the marked increase in HCOO^- bands (1558 and 1350 cm^{-1}) concurrent with the stabilization of DOM peaks indicates that the conversion of adsorbed DOM to HCOO^- is a key photo-driven step. The introduction of humidity (Fig. 9c) significantly accelerates the depletion of DOM signals while further decreasing HCOO^- peaks. It thus suggests that water plays a dual role: it not only generates a higher flux of $\cdot\text{OH}$ radicals that attack DOM but may also facilitate the hydrolysis of this intermediate. The accumulation of HCOO^- species under all conditions implies that its subsequent oxidation to CO_2 and H_2O is likely the rate-limiting step in the overall mineralization pathway. This detailed mechanistic understanding, moving from initial adsorption to the final kinetic bottleneck, is crucial for future strategies aimed at optimizing catalyst surface chemistry to enhance HCOO^- decomposition.

Fig. 9 In-situ DRIFTS spectra of TB-5 under different reaction conditions: (a) FA + air + UV off, (b) FA + air + UV on, and (c) FA + air + H_2O + UV on

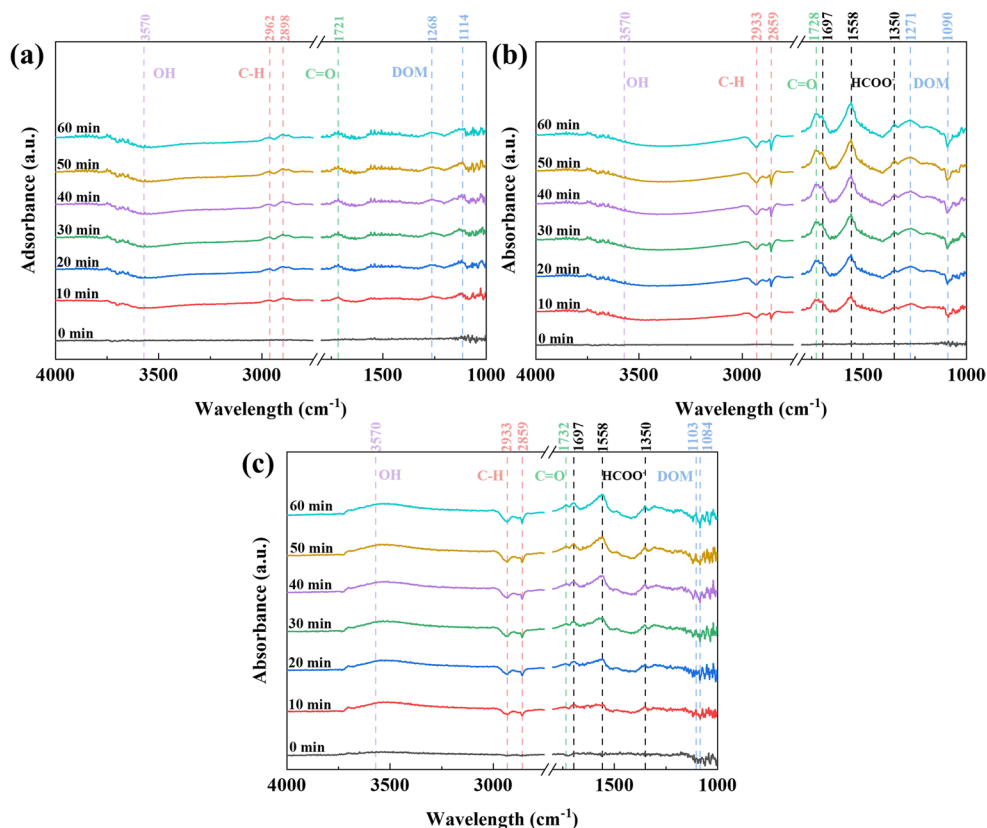

Under UV irradiation at 0% RH level, the marked increase in formate bands at 1558 cm^{-1} and 1350 cm^{-1} concurrent with the stabilization of DOM peaks indicates that the photo-driven conversion of DOM to HCOO^- is a key step (Fig. 9b). The introduction of 20% RH (Fig. 9c) significantly changed the evolution of surface intermediates. Both the DOM and HCOO^- bands decreased in intensity, while the $-\text{OH}$ band near 3570 cm^{-1} increased progressively. This result indicates that water participates in the surface reaction process and modifies the surface coverage of FA-derived species. However, in line with the chamber-scale results, humidity did not improve the overall FA removal performance, indicating that any local participation of water in surface reactions is outweighed by its inhibitory effect on photocatalytic oxidation.

3.4.2 DFT simulation

To elucidate the electron-transfer mechanism in TB-5, density-functional calculations were performed to analyze the band structures, densities of states, work functions, electron-localization function (ELF) and charge-density difference of Bi_2WO_6 , TiO_2 , and the TB-5 heterostructure. The calculated band gaps of Bi_2WO_6 , TiO_2 , and the TB-5 heterostructure are 1.51, 2.54 and 1.61 eV, respectively (Fig. 10a–c). The intermediate value observed for TB-5 reflects the combined electronic character of its constituents. As expected for GGA calculations, all values are slightly lower

than the experimental data, owing to the known tendency of this approximation to underestimate semiconductor band gaps [57]. The projected DOS of TB-5 (Fig. 10d–f) suggests that its CBM and VBM are dominated by the Ti 3d states of TiO_2 and the O 2p states of Bi_2WO_6 , respectively. Crucially, the DFT-calculated $\Delta\Phi$ values are 8.619 eV for Bi_2WO_6 and 7.258 eV for TiO_2 . The discrepancy in $\Delta\Phi$ values arises primarily from the surface-sensitive nature, which depends strongly on slab thickness, vacuum spacing, surface termination, relaxation, and the presence of defects or adsorbates. The $\Delta\Phi$ values derived from UPS are often lower than the DFT-calculated because the catalyst surface is readily affected by contamination under experimental conditions. Therefore, while the absolute values differ, the relative trend remains physically meaningful and can still be used to identify the direction of interfacial charge transfer [58].

This significant difference in $\Delta\Phi$ values between the two components of heterojunction ($\Phi(\text{Bi}_2\text{WO}_6) > \Phi(\text{TiO}_2)$, Fig. 10a–b) predicts that upon contact, electrons will flow from TiO_2 to Bi_2WO_6 until their Fermi levels equilibrate [59]. This process generates an IEF directed from TiO_2 to Bi_2WO_6 , which is the fundamental driving force for the S-scheme mechanism as discussed above in detail. While the absolute DFT values may deviate from experiment due to the use of idealized models and semilocal functionals, the relative trend is physically meaningful and aligns with our UPS results (Fig. 5d–e). This theoretical framework is powerfully corroborated by experimental evidence. The







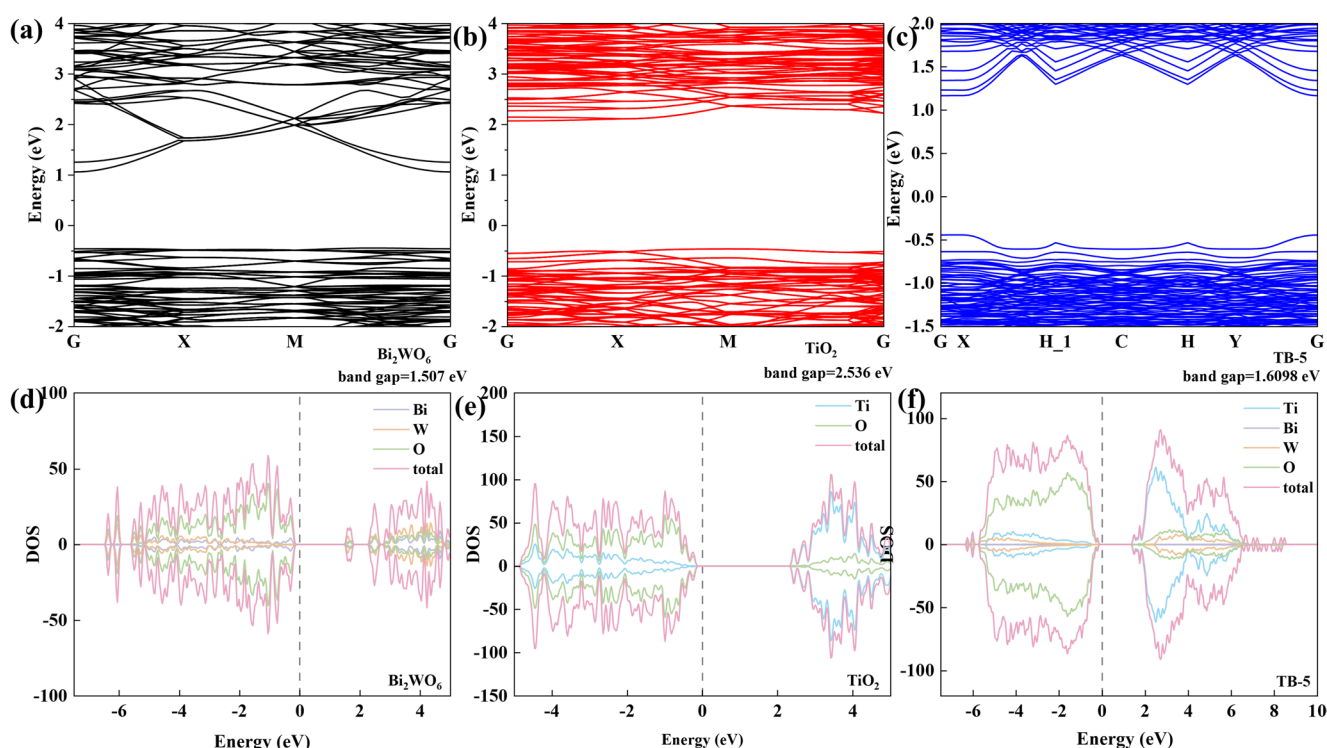


Fig. 10 Calculated band structures: (a) Bi_2WO_6 , (b) TiO_2 and (c) TB-5. DOS curves: (d) Bi_2WO_6 , (e) TiO_2 and (f) TB-5

predicted electron transfer is directly observed in the XPS spectra (Fig. 4a-b), which shows a 0.2 eV blue shift for Ti 2p peaks (electron depletion) and a 0.2 eV red shift for Bi 4f peaks (electron accumulation). Furthermore, the charge-density-difference map calculated via DFT (Fig. 11d) visually confirms this spatial charge redistribution with electron accumulation on Bi_2WO_6 (yellow) and depletion on the TiO_2 side (cyan). In summary, the seamless alignment between DFT predictions and multiple experimental (e.g., XPS and UPS) methods provides a multi-faceted and unequivocal validation of an S-scheme charge transfer pathway in the TB-5 heterojunction.

3.4.3 Photocatalytic mechanism of FA

Based on the in-situ DRIFTS results and photoelectrochemical analysis, the oxidation pathway of FA at the surface of TB-5 S-scheme heterojunction can be explained via the following sequence of reactions [48, 60]. The initial step involves the adsorption and surface reaction of FA, where in-situ DRIFTS confirmed the formation of a dioxymethylene (DOM, $[\text{H}_2\text{CO}_2]_{\text{ads}}$) intermediate. The subsequent steps are driven by the efficient charge separation of the S-scheme heterojunction, which provides a high flux of holes (h^+) for $\cdot\text{OH}$ radical production and electrons (e^-) for $\cdot\text{O}_2^-$ generation, as evidenced by the strong photocurrent response and EIS data.



3.5 Performance comparison between different catalysts

To contextualize the performance of the TB-5 S-scheme heterojunction, its photocatalytic activity was benchmarked against other representative photocatalysts reported for gas-phase formaldehyde oxidation. The comparison, detailed numerically in Table 3, evaluates key performance indicators, including r_{max} , AQY, MAQY, and CADR under comparable conditions. An analysis of the intrinsic and practical kinetic descriptors reveals their superior performance.

The intrinsic kinetic capability of each catalyst was evaluated using the mass-normalized rate, r_{max} ($\text{mmol mg}^{-1} \text{h}^{-1}$). The top five materials of r_{max} rank as follows: N-TiO₂ (0.65) > TB-5 (0.31) > TiO₂-SiC (0.21) > NiO-TiO₂ (0.183) > Cu-TiO₂ (0.07) (Table 3). In terms of r_{max} , which reflects the intrinsic activity per mass of catalyst, TB-5 is a top-tier material, outperforming only by N-TiO₂.

Fig. 11 Calculated work functions of (a) Bi_2WO_6 and (b) TiO_2 . (c) Electron localization function of TB-5 and (d) Charge density difference of TB-5 with an iso-surface of 0.002 e/Bohr³

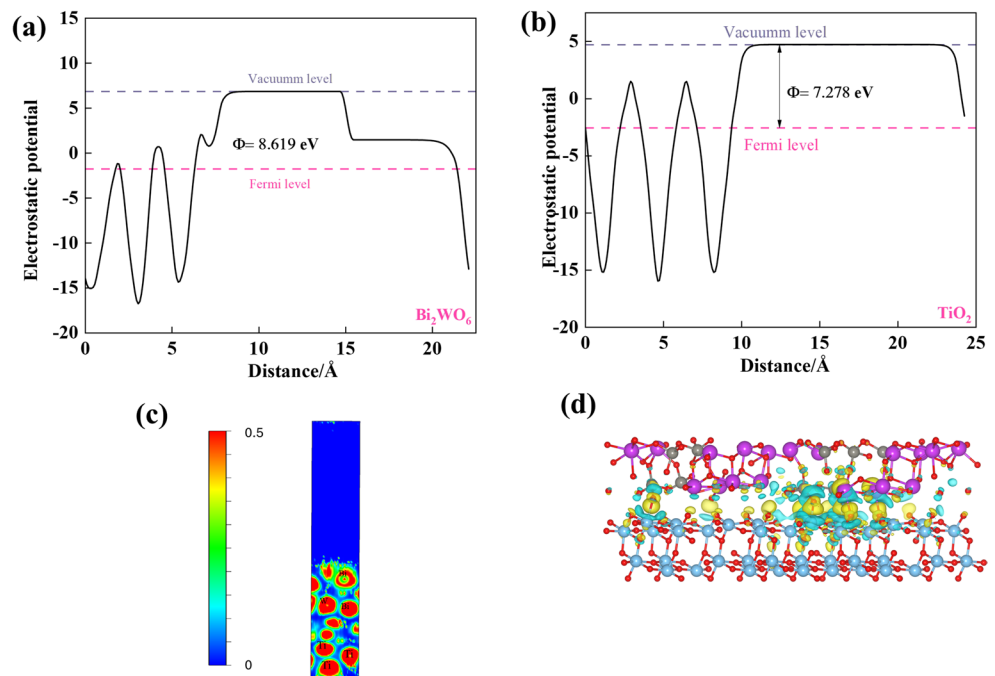


Table 3 The removal performance of FA between different photocatalytic systems (TB-5 vs. ones reported previously)

Order	Catalyst	Light source	m_{cat}	FA concentration	Irradiation time	X_{FA}	r_{max}	AQY	MAQY	CADR	Reference
			(mg)	(ppm)	(h)	(%)	(mmol $\text{mg}^{-1} \text{h}^{-1}$)	(%)	(molecules $\text{photon}^{-1} \text{g}^{-1}$)	(L min^{-1})	
1	Cu-TiO ₂	500 W Xe lamp	100	250	2.33	100	0.07	9.70E-04	9.70E-03	-	[61]
2	NiO-TiO ₂	1 W UV lamp	81.3	1	0.1	100	0.085	6.34E-02	7.79E-03	10.35	[48]
3	NiO-TiO ₂	1 W UV lamp		5	0.17	100	0.183	1.36E-01	1.62E-02	6.55	[48]
4	Bi-TiO ₂	300 W Xe lamp	30	40	0.25	93	0.02	1.60E-05	5.35E-06	0.02	[62]
5	BiVO ₄ OVs-MIL-88 A(Fe)	30 W Xe lamp	200	50	2	91.8	0.03	1.47E-03	7.36E-05	0.12	[63]
6	N-TiO ₂	1 W UV lamp	59.9	5	0.08	93	0.65	3.54E-01	5.90E-02	9.45	[9]
7	TiO ₂ -SiC	1 W UV lamp	100	1	0.03	100	0.21	1.90E-01	1.90E-02	18.53	[64]
8	TiO ₂ -SiC	1 W UV lamp	100	5	0.17	90	0.2	1.75E-01	1.75E-02	8.45	[64]
9	TiO ₂ /C/CaCO ₃	300 W Xe lamp	200	358	1.33	100	0.05	2.89E-04	1.45E-05	0.37	[65]
10	TB-5	1 W UV lamp	83.8	1	0.05	100	0.23	1.79E-01	2.13E-02	21.09	This study
11	TB-5	1 W UV lamp	83.8	5	0.17	100	0.35	2.68E-01	3.20E-02	10.37	This study

The CADR (L min^{-1}) represents a standardized, device-level parameter that characterizes the practical throughput of an air purifier system, making it a crucial metric for benchmarking real-world applicability. Comparison of CADR demonstrates TB-5's practical superiority. TB-5 achieves a CADR of 21.09 L min^{-1} at 1 ppm and 10.37 L min^{-1} at 5 ppm, the highest value among the catalysts evaluated. This performance significantly surpasses that of all other catalysts under low-concentration conditions. This establishes that while TB-5 has exceptional intrinsic kinetics, its practical cleaning efficiency is unmatched. Furthermore, the data highlights a key limitation of CADR: it exhibits a strong inverse relationship with initial FA concentration, as seen with TB-5, TiO₂-SiC, and NiO-TiO₂, whose CADR values drop substantially when concentration increases from 1 to 5 ppm.

Finally, the trend in kinetic superiority is corroborated by the AQY. AQY represents a practical tool for gauging photocatalyst effectiveness while providing essential metrics for cross-comparison among experiments conducted under various conditions [66]. Here, TB-5 developed in this work is found as the top-performing performer for AQY (%), while a similar relative trend is observed: N-TiO₂ (3.54×10^{-1}) > TB-5 (2.68×10^{-1}) > TiO₂-SiC (1.90×10^{-1}) > NiO-TiO₂ (1.36×10^{-1}) > BiVO₄ OVs-MIL-88 A(Fe) (1.47×10^{-3}). To address the limitation that AQY omits catalyst mass considerations, MAQY (molecules $\text{photon}^{-1} \text{g}^{-1}$) is presented alongside, offering a mass-weighted photonic efficiency parameter. The MAQY ranking follows the same order: N-TiO₂ (5.90×10^{-2}) > TB-5 (3.20×10^{-2}) > TiO₂-SiC (1.90×10^{-2}) > NiO-TiO₂ (1.62×10^{-2}) > Cu-TiO₂ (9.70×10^{-3}). Here, TB-5 (3.20×10^{-2}) at 5 ppm again ranks

second only to N-TiO₂, confirming its high efficiency in converting light into chemical activity.

Collectively, the performance evaluation based on these key metrics demonstrates that TB-5 generally achieves outstanding FA removal across the full spectrum of evaluation criteria. The leading CADR value translates this material-level excellence into a practical, device-level performance advantage. Further, high r_{max} also supports its intrinsic kinetic superiority at the material level. In addition, the outstanding AQY demonstrates its exceptional efficiency in converting photons into chemical reactions. In summary, TB-5 consistently ranks as one of the most kinetically capable and efficient photocatalysts, with its standout advantage being the highest practical CADR at low, realistic pollutant levels. This comprehensive outperformance indicates that TB-5 effectively integrates rapid surface kinetics with efficient photon-to-molecule conversion and high device-level throughput, establishing it as a truly promising catalyst for real-world applications.

4 Conclusions

In this study, a well-defined TiO₂-Bi₂WO₆ S-scheme heterojunction (TB-5) was successfully engineered and demonstrated outstanding capability for gaseous formaldehyde (FA) abatement. Photoelectrochemical measurements revealed that TB-5 exhibited higher photocurrent density ($86 \mu\text{A cm}^{-2}$) and lower charge-transfer resistance (3.35Ω) than TiO₂ ($24 \mu\text{A cm}^{-2}$, 5.60Ω) or Bi₂WO₆ ($20 \mu\text{A cm}^{-2}$, 6.60Ω). Under 0.98 W UV irradiation in a portable air-purification reactor, TB-5 could achieve 100% X_{FA} within 600 s,

with a CADR value of 10.37 L min^{-1} and a SCADR value of $123.80 \text{ L min}^{-1} \text{ g}^{-1}$, respectively. The AQY/MAQY also showed the highest value of $2.68\text{E-}01\%$ and $3.20\text{E-}02$ molecules $\text{photon}^{-1} \text{ g}^{-1}$, which is 2.3/2.6 times and 1.3/1.6 times better than its pristine components of Bi_2WO_6 and TiO_2 , respectively. This enhanced performance is attributed to the formation of a highly efficient S-scheme heterojunction at the TB-5 interface, which preserves strongly oxidative holes in the Bi_2WO_6 VB and highly reductive electrons in the TiO_2 CB, thereby maximizing ROS ($\cdot\text{O}_2^-/\cdot\text{OH}$) generation and utilization. This unique charge transfer pathway not only accelerates FA oxidation kinetics but also ensures the retention of strong redox capability essential for complete mineralization. This catalyst exhibited sustained activity over 5 cycles and maintained optimal performance at moderate hydrothermal synthesis durations (15 h), confirming both structural and electronic robustness. In-situ DRIFTS analysis elucidated the photocatalytic oxidation for TB-5 via a clear stepwise pathway, which proceeds through three sequential steps: (i) FA adsorption on the surface $\cdot\text{OH}$ of TB-5, (ii) adsorbed FA converts to DOM, followed by reaction with ROS to yield formate intermediates (HCOO^-), and (iii) complete mineralization to CO_2 and H_2O . Through the integration of experimental characterization and DFT modeling, we have validated the heterostructure design and elucidated the underlying charge transfer mechanism governing the enhanced photocatalytic activity of TB-5. Although this study is still limited by its evaluation under controlled laboratory conditions with single-component FA and UV-driven operation, these findings are inspired to establish formidable future optimization strategies for the efficient abatement of indoor VOCs.

Supplementary Information The online version contains supplementary material available at <https://doi.org/10.1007/s42114-026-01932-2>.

Author contributions Q.Y.: Conceptualization; Investigation; Data curation; Writing - original draft & editing. H.A.M.: Validation, Formal analysis, Writing review & editing. K.H.K.: Investigation; Conceptualization, Methodology; Project administration; Resources; Software; Supervision; Validation; Visualization; Writing - review & editing.

Funding This work was supported by a grant from the National Research Foundation of Korea (NRF) funded by the Ministry of Science and ICT (MSIT) of the Korean government (Grant No: 2021R1A3B1068304). Additional support was provided by the Regional Innovation System & Education (RISE) program through the Seoul RISE Center, funded by the Ministry of Education (MOE) and the Seoul Metropolitan Government (Grant No. 2026-RISE-01-027-01). This research was also supported by the Center for Polymers and Composite Materials (CPCM), Hanyang University, through the Korea Basic Science Institute (National Research Facilities and Equipment Center), funded by the Ministry of Education (Grant No: 2022R1A-6C101A779). The SEM-EDS measurements using the Sigma 300 (Carl Zeiss) were supported by CPCM.

Data availability The data that supports the findings of this study will be available on proper request.

Declarations

Competing interests The authors declare no competing interests.

Open Access This article is licensed under a Creative Commons Attribution-NonCommercial-NoDerivatives 4.0 International License, which permits any non-commercial use, sharing, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons licence, and indicate if you modified the licensed material. You do not have permission under this licence to share adapted material derived from this article or parts of it. The images or other third party material in this article are included in the article's Creative Commons licence, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons licence and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this licence, visit <http://creativecommons.org/licenses/by-nc-nd/4.0/>.

References

- Bourguignon M, Grignard B, Detrembleur C (2021) Introducing polyhydroxyurethane hydrogels and coatings for formaldehyde capture. *ACS Appl Mater Interfaces* 13:54396–54408. <https://doi.org/10.1021/acsami.1c16917>
- Wang T, Wang H, Xia P, Xue S, Yang G, Li H, Li Z, Jiang X, Xing X (2021) PVA-SM microstructure enhanced ratiometric fluorescence probe for formaldehyde detection in solution and gas. *Opt Lett* 46:5759–5762. <https://doi.org/10.1364/OL.441296>
- Hu D, Tobon Y, Agostini A, Grosselin B, Chen Y, Robin C, Yahyaoui A, Colin P, Mellouki A, Daële V (2022) Diurnal variation and potential sources of indoor formaldehyde at elementary school, high school and university in the Centre Val de Loire region of France. *Sci Total Environ* 811:152271. <https://doi.org/10.1016/j.scitotenv.2021.152271>
- Peng W-X, Yue X, Chen H, Ma NL, Quan Z, Yu Q, Wei Z, Guan R, Lam SS, Rinklebe J, Zhang D, Zhang B, Bolan N, Kirkham MB, Sonne C (2022) A review of plants formaldehyde metabolism: implications for hazardous emissions and phytoremediation. *J Hazard Mater* 436:129304. <https://doi.org/10.1016/j.jhazmat.2022.129304>
- Wojnowski W, Yang A, Mikoviny T, Wisthaler A, Thunshelle K (2024) Exposure to cooking emitted volatile organic compounds with recirculating and extracting ventilation solutions. *Build Environ* 261:111743. <https://doi.org/10.1016/j.buildenv.2024.111743>
- Nielsen GD, Larsen ST, Wolkoff P (2017) Re-evaluation of the WHO (2010) formaldehyde indoor air quality guideline for cancer risk assessment. *Arch Toxicol* 91:35–61. <https://doi.org/10.1007/s00204-016-1733-8>
- Hua Y, Vikrant K, Kim K-H, Heynderickx PM, Boukhvalov DW (2025) Room temperature thermocatalytic removal of formaldehyde in air using a copper manganite spinel-supported palladium catalyst with ultralow noble metal content. *Sep Purif Technol* 354:128863. <https://doi.org/10.1016/j.seppur.2024.128863>
- Qian R, Zong H, Schneider J, Zhou G, Zhao T, Li Y, Yang J, Bahnemann DW, Pan JH (2019) Charge carrier trapping, recombination and transfer during TiO_2 photocatalysis: an overview. *Catal Today* 335:78–90. <https://doi.org/10.1016/j.cattod.2018.10.053>

9. Lim D-H, Bathla A, Anwer H, Younis SA, Boukhalov DW, Kim K-H (2024) The effects of nitrogen-doping on photocatalytic mineralization of TiO₂ nanocatalyst against formaldehyde in ambient air. *Chin J Catal* 59:303–323. [https://doi.org/10.1016/S1872-2067\(24\)60010-0](https://doi.org/10.1016/S1872-2067(24)60010-0)
10. Maitlo HA, Anand B, Kim K-H (2024) TiO₂-based photocatalytic generation of hydrogen from water and wastewater. *Appl Energy* 361:122932. <https://doi.org/10.1016/j.apenergy.2024.122932>
11. Maitlo HA, Hu Z, Ali I, Maitlo G, Lim D-H, Afridi MN, Zhou M (2024) Recent development in advanced photocatalytic materials for oxidative removal of bisphenol. *J Clean Prod* 434:140291. <https://doi.org/10.1016/j.jclepro.2023.140291>
12. Ali Maitlo H, Younis SA, Kim K-H (2025) Understanding oxidation potential and degradation mechanism of acid-treated TiO₂ coupled g-C₃N₄ S-scheme heterojunction photocatalyst for the removal of gaseous formaldehyde. *Sep Purif Technol* 356:129862. <https://doi.org/10.1016/j.seppur.2024.129862>
13. Zhang Y, Wang D, Luo X, Chen Y, Lei K, Mao L, Duan Y, Zeng X, Wan G, Zhao Q, Sun Y (2024) Facile construction of Bi₂WO₆/TiO₂ microspheres heterojunction for boosting photocatalytic degradation of organic dyes. *Inorg Chem Commun* 165:112543. <https://doi.org/10.1016/j.inoche.2024.112543>
14. Rong A, Shi H, Zhao Q, Zhu H, Wang H, Yan G (2024) Boosted photocatalytic performance of hydrogen evolution and formaldehyde degradation with a S-scheme PMo₁₂/MgIn₂S₄ heterojunction. *Sep Purif Technol* 348:127782. <https://doi.org/10.1016/j.seppur.2024.127782>
15. Kovalevskiy N, Cherepanova S, Gerasimov E, Lyulyukin M, Solovyeva M, Prosvirin I, Kozlov D, Selishchev D (2022) Enhanced photocatalytic activity and stability of Bi₂WO₆-TiO₂-N nanocomposites in the oxidation of volatile pollutants. *Nanomaterials (Basel)*. <https://doi.org/10.3390/nano12030359>
16. Collado L, Gomez-Mendoza M, Garcia-Tecedor M, Oropeza FE, Reynal A, Durrant JR, Serrano DP, de la Peña O'Shea VA (2023) Towards the improvement of methane production in CO₂ photoreduction using Bi₂WO₆/TiO₂ heterostructures. *Appl Catal B Environ* 324:122206. <https://doi.org/10.1016/j.apcatb.2022.122206>
17. Yang H, Zhao S, Zhuang X, Asuha S (2022) Hydrothermal synthesis of Bi₂WO₆/mesoporous TiO₂ nanocomposites and their adsorptive properties. *J Nanopart Res* 24:159. <https://doi.org/10.1007/s11051-022-05430-6>
18. Zhu Z, Wan S, Zhao Y, Qin Y, Ge X, Zhong Q, Bu Y (2021) Recent progress in Bi₂WO₆-based photocatalysts for clean energy and environmental remediation: competitiveness, challenges, and future perspectives. *Nano Sel* 2(2):187–215. <https://doi.org/10.1002/nano.202000127>
19. Shang M, Wang W, Zhang L, Sun S, Wang L, Zhou L (2009) 3D Bi₂WO₆/TiO₂ hierarchical heterostructure: controllable synthesis and enhanced visible photocatalytic degradation performances. *J Phys Chem C* 113:14727–14731. <https://doi.org/10.1021/jp9045808>
20. Murcia López S, Hidalgo MC, Navío JA, Colón G (2011) Novel Bi₂WO₆-TiO₂ heterostructures for rhodamine B degradation under sunlight irradiation. *J Hazard Mater* 185:1425–1434. <https://doi.org/10.1016/j.jhazmat.2010.10.065>
21. Xu J, Wang W, Sun S, Wang L (2012) Enhancing visible-light-induced photocatalytic activity by coupling with wide-band-gap semiconductor: A case study on Bi₂WO₆/TiO₂. *Appl Catal B* 111–112:126–132. <https://doi.org/10.1016/j.apcatb.2011.09.025>
22. Yao L, Wang W, Liang Y, Fu J, Shi H (2019) Plasmon-enhanced visible light photoelectrochemical and photocatalytic activity of gold nanoparticle-decorated hierarchical TiO₂/Bi₂WO₆ nanorod arrays. *Appl Surf Sci* 469:829–840. <https://doi.org/10.1016/j.apsusc.2018.11.031>
23. Chang H, Jiang M, Zhu Q, Liu A, Wu Y, Li C, Ji X, Gong L, Li S, Chen Z, Kong L, Han L (2022) A novel photoelectrochemical immunosensor based on TiO₂@Bi₂WO₆ hollow microspheres and Ag₂S for sensitive detection of SARS-COV-2 nucleocapsid protein. *Microchem J* 182:107866. <https://doi.org/10.1016/j.micro.2022.107866>
24. Ahmadi M, Alavi SM, Larimi A (2023) UV–vis light responsive Bi₂WO₆ nanosheet/TiO₂ nanobelt heterojunction photo-catalyst for CO₂ reduction. *Catal Commun* 179:106681. <https://doi.org/10.1016/j.catcom.2023.106681>
25. Jia Y, Zhan S, Ma S, Zhou Q (2016) Fabrication of TiO₂-Bi₂WO₆ binanosheet for enhanced solar photocatalytic disinfection of *E. coli*: insights on the mechanism. *ACS Appl Mater Interfaces* 8:6841–6851. <https://doi.org/10.1021/acsami.6b00004>
26. Chai Y, Zhou F, Zhu Z (2019) High-efficiency and environment-friendly sterilization PEVE coatings modified with Bi₂WO₆/TiO₂ composites. *Chem Phys Lett* 715:173–180. <https://doi.org/10.1016/j.cplett.2018.11.046>
27. Mamaghani AH, Haghighat F, Lee C-S (2017) Photocatalytic oxidation technology for indoor environment air purification: the state-of-the-art. *Appl Catal B Environ* 203:247–269. <https://doi.org/10.1016/j.apcatb.2016.10.037>
28. Li Y-W, Ma W-L (2021) Photocatalytic oxidation technology for indoor air pollutants elimination: a review. *Chemosphere* 280:130667. <https://doi.org/10.1016/j.chemosphere.2021.130667>
29. Zhang M (2020) Synthesis of Bi₂WO₆/TiO₂ flake nano-heterostructure photocatalyst and its photocatalytic performance under visible light irradiation. *J Mater Sci: Mater Electron* 31:20129–20138. <https://doi.org/10.1007/s10854-020-04534-w>
30. Khanam S, Rout SK (2022) Enhanced photocatalytic oxidation of RhB and MB using plasmonic performance of Ag deposited on Bi₂WO₆. *Chemistry (Weinheim an der Bergstrasse, Germany)*. <https://doi.org/10.3390/chemistry4020022>
31. Trixy Nimmy Priscilla D, Radha R, Chitra A, Geetha S.K. (2024) Comprehensive evaluation of nanosized bismuth tungstate (Bi₂WO₆) as photoanodes for photoelectrochemical water splitting performance. *J Cluster Sci* 35:875–889. <https://doi.org/10.1007/s10876-023-02520-w>
32. Du Z, Cheng C, Tan L, Lan J, Jiang S, Zhao L, Guo R (2018) Enhanced photocatalytic activity of Bi₂WO₆/TiO₂ composite coated polyester fabric under visible light irradiation. *Appl Surf Sci* 435:626–634. <https://doi.org/10.1016/j.apsusc.2017.11.136>
33. Hao X, Zhou J, Cui Z, Wang Y, Wang Y, Zou Z (2018) Zn-vacancy mediated electron-hole separation in ZnS/g-C₃N₄ heterojunction for efficient visible-light photocatalytic hydrogen production. *Appl Catal B Environ* 229:41–51. <https://doi.org/10.1016/j.apcatb.2018.02.006>
34. Zhang L, Meng G, Liu B, Ge X (2022) Heterogeneous photocatalytic ozonation of sulfamethoxazole by Z-scheme Bi₂WO₆/TiO₂ heterojunction: performance, mechanism and degradation pathway. *J Mol Liq* 360:119427. <https://doi.org/10.1016/j.molliq.2022.119427>
35. D'Amato CA, Giovannetti R, Zannotti M, Rommozzi E, Minicucci M, Gunnella R, Di Cicco A (2018) Band Gap Implications on Nano-TiO₂ Surface Modification with Ascorbic Acid for Visible. Light-Active Polypropylene Coated Photocatalyst, Nanomaterials. <https://doi.org/10.3390/nano8080599>
36. Zhou Y, Zhang Y, Lin M, Long J, Zhang Z, Lin H, Wu JCS, Wang X (2015) Monolayered Bi₂WO₆ nanosheets mimicking heterojunction interface with open surfaces for photocatalysis. *Nat Commun* 6:8340. <https://doi.org/10.1038/ncomms9340>
37. Chen L, Ren J-T, Yuan Z-Y (2023) Enabling internal electric fields to enhance energy and environmental catalysis. *Adv Energy Mater* 13:2203720. <https://doi.org/10.1002/aenm.202203720>
38. Khatun S, Pal S, Roy P (2024) Surface oxygen vacancy engineering of Cr-doped FeNi₃/NiFe₂O₄ Mott-Schottky heterojunction as efficient electrocatalyst for high current density water oxidation. *J*

- Alloys Compd 977:173393. <https://doi.org/10.1016/j.jallcom.2023.173393>
39. Lasia A (2014) Semiconductors and Mott-Schottky Plots. In: Lasia A (ed) *Electrochemical Impedance Spectroscopy and its Applications*. Springer New York, New York, NY, pp 251–255
 40. Bhat SS, M, S G K (2025) Recent advances in interface engineering of bismuth-based materials for photocatalytic CO₂ reduction. *RSC Applied Interfaces*. <https://doi.org/10.1039/D5LF00154D>
 41. Li B, Liu X-j, Zhu H-w, Guan H-p, Guo R-t (2024) A review on Bi₂WO₆-based materials for photocatalytic CO₂ reduction. *Small* 20:2406074. <https://doi.org/10.1002/sml.202406074>
 42. Wen S, Zhang W, Yang J, Zhou Z, Xiang Q, Dong H (2024) Ternary Bi₂WO₆/TiO₂-Pt heterojunction sonosensitizers for boosting sonodynamic therapy. *ACS Nano* 18:23672–23683. <https://doi.org/10.1021/acsnano.4c08236>
 43. Parrino F, Livraghi S, Giamello E, Ceccato R, Palmisano L (2020) Role of hydroxyl, superoxide, and nitrate radicals on the fate of bromide ions in photocatalytic TiO₂ suspensions. *ACS Catal* 10:7922–7931. <https://doi.org/10.1021/acscatal.0c02010>
 44. Palominos R, Freer J, Mondaca MA, Mansilla HD (2008) Evidence for hole participation during the photocatalytic oxidation of the antibiotic flumequine. *J Photochem Photobiol A Chem* 193:139–145. <https://doi.org/10.1021/acscatal.0c02010>
 45. Leng WH, Zhang Z, Zhang JQ, Cao CN (2005) Investigation of the kinetics of a TiO₂ photoelectrocatalytic reaction involving charge transfer and recombination through surface states by electrochemical impedance spectroscopy. *J Phys Chem B* 109:15008–15023. <https://doi.org/10.1021/jp051821z>
 46. Meng S, Zhang J, Chen S, Zhang S, Huang W (2019) Perspective on construction of heterojunction photocatalysts and the complete utilization of photogenerated charge carriers. *Appl Surf Sci* 476:982–992. <https://doi.org/10.1016/j.apsusc.2019.01.246>
 47. Jing L, Qu Y, Wang B, Li S, Jiang B, Yang L, Fu W, Fu H, Sun J (2006) Review of photoluminescence performance of nano-sized semiconductor materials and its relationships with photocatalytic activity. *Sol Energy Mater Sol Cells* 90:1773–1787. <https://doi.org/10.1016/j.solmat.2005.11.007>
 48. Lu Y, Younis SA, Chen C, Lu Z, Kim K-H (2025) Unveiling an inverted S-scheme pathway in nickel oxide/titanium dioxide for enhanced photocatalytic oxidation of gaseous formaldehyde. *Compos Part B Eng* 306:112834. <https://doi.org/10.1016/j.composb.2025.112834>
 49. Masresha G, Jabasingh SA, Kebede S, Doo-Arhin D, Assefa M (2023) A review of prospects and challenges of photocatalytic decomposition of volatile organic compounds (VOCs) under humid environment. *Can J Chem Eng* 101:6905–6918. <https://doi.org/10.1002/cjce.24978>
 50. Sun S, Vikrant K, Verma S, Boukhvalov DW, Kim K-H (2024) Diaminopropane-appended activated carbons for the adsorptive removal of gaseous formaldehyde using a portable indoor air purification unit. *J Colloid Interface Sci* 653:992–1005. <https://doi.org/10.1016/j.jcis.2023.09.159>
 51. Jeong M-G, Park EJ, Seo HO, Kim K-D, Kim YD, Lim DC (2013) Humidity effect on photocatalytic activity of TiO₂ and regeneration of deactivated photocatalysts. *Appl Surf Sci* 271:164–170. <https://doi.org/10.1016/j.apsusc.2013.01.155>
 52. Malayeri M, Haghighat F, Lee C-S (2019) Modeling of volatile organic compounds degradation by photocatalytic oxidation reactor in indoor air: a review. *Build Environ* 154:309–323. <https://doi.org/10.1016/j.buildenv.2019.02.023>
 53. Jiang X, Xu W, Yu L (2019) Photocatalytic decomposition of gaseous HCHO over Ag modified TiO₂ nanosheets at ambient temperature. *Nanomaterials (Basel)*. <https://doi.org/10.3390/nano9030338>
 54. Yu J, Yu H, Cheng B, Zhou M, Zhao X (2006) Enhanced photocatalytic activity of TiO₂ powder (P25) by hydrothermal treatment. *J Mol Catal A Chem* 253:112–118. <https://doi.org/10.1016/j.molcata.2006.03.021>
 55. Nagyné-Kovács T, Shahnazarova G, Lukács IE, Szabó A, Hernádi K, Igricz T, László K, Szilágyi IM, Pokol G (2019) Effect of pH in the Hydrothermal Preparation of Bi₂WO₆ Nanostructures. *Materials (Basel)* 12. <https://doi.org/10.3390/ma12111728>
 56. Li N, Huang B, Dong X, Luo J, Wang Y, Wang H, Miao D, Pan Y, Jiao F, Xiao J, Qu Z (2022) Bifunctional zeolites-silver catalyst enabled tandem oxidation of formaldehyde at low temperatures. *Nat Commun* 13:2209. <https://doi.org/10.1038/s41467-022-29936-8>
 57. Hao B, Ahmadi Y, Zhang T, Chen C, Lu Z, Ma H, Kim K-H (2025) Ultrathin K-doped g-C₃N₄/BiOBr heterojunctions with S-scheme charge transfer for efficient photodegradation of tetracycline. *J Environ Manage* 391:126677. <https://doi.org/10.1016/j.jenvman.2025.126677>
 58. Olawole OC, De DK, Olawole OF, Lamba R, Joel ES, Oyedepo SO, Ajayi AA, Adegbite OA, Ezema FI, Naghdi S, Olawole TD, Obembe OO, Oguniran KO (2022) Progress in the experimental and computational methods of work function evaluation of materials: a review. *Heliyon* 8:e11030. <https://doi.org/10.1016/j.heliyon.2022.e11030>
 59. Lejaeghere K, Van Speybroeck V, Van Oost G, Cottenier S (2014) Error estimates for solid-state density-functional theory predictions: an overview by means of the ground-state elemental crystals. *Crit Rev Solid State Mater Sci* 39:1–24. <https://doi.org/10.1080/10408436.2013.772503>
 60. Tasbihi M, Bendyna JK, Notten PHL, Hintzen HT (2015) A short review on photocatalytic degradation of formaldehyde. *J Nanosci Nanotechnol* 15:6386–6396. <https://doi.org/10.1166/jnn.2015.10872>
 61. Chen M, Wang H, Chen X, Wang F, Qin X, Zhang C, He H (2020) High-performance of Cu-TiO₂ for photocatalytic oxidation of formaldehyde under visible light and the mechanism study. *Chem Eng J* 390:124481. <https://doi.org/10.1016/j.cej.2020.124481>
 62. Ma L, Huang C, Li X, An X, Li J, Zou L, Zhu X, Yuan C, Dai X, Zhou Y, Zhu X, Tian C (2025) In situ synthesis of mesoporous TiO₂ doped with bismuth single atoms for tunable photocatalytic degradation of formaldehyde. *Sep Purif Technol* 354:128635. <https://doi.org/10.1016/j.seppur.2024.128635>
 63. Jiang Z, Wang T, Wang J, Yu T, Kong C, Yang Z, Zhu H (2025) Oxygen vacancy-rich BiVO₄ modified with mesoporous MIL-88A(Fe) Z-scheme heterojunction for enhanced photocatalytic formaldehyde degradation. *Sep Purif Technol* 353:128581. <https://doi.org/10.1016/j.seppur.2024.128581>
 64. He X, Vikrant K, Boukhvalov DW, Kim K-H (2025) Synthesis, performance, and reaction mechanisms of titanium dioxide-silicon carbide as a step-scheme heterojunction photocatalyst against formaldehyde in air. *Chem Eng J* 519:164114. <https://doi.org/10.1016/j.cej.2025.164114>
 65. Qiu S, Wang W, Yu J, Tian X, Li X, Deng Z, Lin F, Zhang Y (2022) Enhanced photocatalytic degradation efficiency of formaldehyde by in-situ fabricated TiO₂/C/CaCO₃ heterojunction photocatalyst from mussel shell extract. *J Solid State Chem* 311:123110. <https://doi.org/10.1016/j.jssc.2022.123110>
 66. Wang C, Ge B, Jiang P, Xu F, Cheng C, Huang C (2025) Photocatalytic apparent quantum yield exceeding 100% achieved by photo-thermal synergistic impact ionization. *Appl Surf Sci* 690:162638. <https://doi.org/10.1016/j.apsusc.2025.162638>

Publisher's note Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.